



Visible-Light-Driven g-C₃N₄/TiO₂ Based Heterojunction Nanocomposites for Photocatalytic Degradation of Organic Dyes in Wastewater: A Review

Authors: Sewnet, Agidew, Abebe, Mulualem, Asaithambi, Perumal, and Alemayehu, Esayas

Source: Air, Soil and Water Research, 15(1)

Published By: SAGE Publishing

URL: <https://doi.org/10.1177/11786221221117266>

BioOne Complete (complete.BioOne.org) is a full-text database of 200 subscribed and open-access titles in the biological, ecological, and environmental sciences published by nonprofit societies, associations, museums, institutions, and presses.

Visible-Light-Driven g-C₃N₄/TiO₂ Based Heterojunction Nanocomposites for Photocatalytic Degradation of Organic Dyes in Wastewater: A Review

Air, Soil and Water Research
Volume 15: 1–23
© The Author(s) 2022
Article reuse guidelines:
sagepub.com/journals-permissions
DOI: 10.1177/11786221221117266



Agidew Sewnet^{1,2} , Mulualem Abebe¹, Perumal Asaithambi³ and Esayas Alemayehu^{3,4}

¹Faculty of Materials Science and Engineering, Jimma University, Jimma, Ethiopia, ²Department of Physics, College of Natural and Computational Science, Bonga University, Bonga, Ethiopia,

³Faculty of Civil and Environmental Engineering, Jimma University, Jimma, Ethiopia, and ⁴Africa Center of Excellence for Water Management, Addis Ababa University, Addis Ababa, Ethiopia

ABSTRACT: Water pollution by organic contaminants is one of the most severe issues confronting the world today as a result of the rapid increase of industrialization, urbanization, human population growth, and advances in agricultural technologies. Several attempts have been made to address global water pollution issues by utilizing conventional wastewater treatment technologies. However, conventional wastewater treatment methods have several limitations such as low efficiency, high operation costs, generation of secondary waste, require additional chemicals as oxidants and extra energy. Therefore, Heterogeneous photocatalysis has gained a lot of attention in the degradation of persistent organic pollutants because it combines high efficiency, environmental friendliness, cheap cost, and safety. Subsequently, the designing of novel nanocomposite photocatalysts with strong visible light-harvesting ability, efficient charge separation and transportation, and superb stability is imminently desired for wastewater treatment. Recently, the notion of combining g-C₃N₄ with TiO₂ to design high photocatalytic performance heterojunction photoactive nanocomposites for organic pollutant degradation has received a lot of attention. Meanwhile, the construction of g-C₃N₄/TiO₂-based heterojunction nanocomposites may enhance the ability of harvesting visible light, boost charge separation and transfer efficiency, and robust photocatalytic activity. Firstly, this review concisely explained the main sources of water pollution, as well as potential treatment approaches and the fundamental mechanism of heterogeneous photocatalysis. Subsequently, the details of properties, synthesis techniques, photoactivity modification strategies, and photocatalytic applications of g-C₃N₄, TiO₂, and g-C₃N₄/TiO₂ heterojunction photocatalysts are presented. Following that, the recent advances aimed at improving the photocatalytic performance of various types of visible-light-driven g-C₃N₄/TiO₂ heterojunction photocatalysts for organic pollutant degradation in wastewater are presented in detail. Finally, some concluding remarks and perspectives on the challenges and opportunities for constructing different types of g-C₃N₄/TiO₂-based heterostructured photocatalysts are presented.

KEYWORDS: Organic contaminants, photocatalytic process, g-C₃N₄/TiO₂, pollutant degradation

RECEIVED: March 16, 2022. **ACCEPTED:** July 7, 2022.

TYPE: Review

CORRESPONDING AUTHORS: Perumal Asaithambi, Faculty of Civil and Environmental Engineering, Jimma University, P.O. Box 378, Jimma, Ethiopia. Email: drasaithambi2014@gmail.com

Esayas Alemayehu, Faculty of Civil and Environmental Engineering, Jimma University, P.O. Box 378, Jimma, Ethiopia. Email: esayas16@yahoo.com

Introduction

Nowadays, the growing global energy demand and increasing water pollution are the most serious problems presently faced worldwide due to the rampant unregulated development of industrialization, improvements in agricultural technologies, and depletion of non-renewable fossil fuels by the increase of the human population (Bustillo-Lecompte, 2015; Darkwah & Oswald, 2019; Gusain et al., 2019; Ong et al., 2016; Xu, Zhang, et al., 2018). Water is majorly polluted due to randomly discharged industrial effluents and anthropogenic activities (Gusain et al., 2019; Thines et al., 2017; Zhang, Gu, et al., 2019). Therefore, the availability of safe drinkable water free from hazardous materials, carcinogenic substances, and harmful germs has become a serious global concern (Ahmed & Haider, 2018; Manikandan et al., 2021). Moreover, the wastewater contains several types of pollutants such as organic (dyes, pesticides, pharmaceutical ingredients, fertilizers, organohalides, phenols, surfactants, etc.), inorganic (heavy metal ions, metal oxides, metal complexes, salts, etc.), nutrients, and agricultural runoff, pathogens, and so on (Gusain et al., 2019;

Thines et al., 2017; Varma et al., 2020; Zhang, Gu, et al., 2019). However, organic pollutants are responsible for major contamination of the environment due to their frequent discharge into the environment. Meanwhile, organic pollutants are prevalent in sewage effluents, groundwater, drinking water, and sludge, posing a serious hazard to people and aquatic creatures (Mahlambi et al., 2015). Therefore, organic pollutants can seriously harm the environment and cause negative effects on human health (Byrne et al., 2018; Low, Jiang, et al., 2017). Some organic pollutants are classified as persistent organic pollutants because they do not readily degrade in the environment and can persist for long periods (Mahlambi et al., 2015). Meanwhile, persistent organic pollutants were known as a kind of organic chemical contamination with high toxicity, which contaminates underground water a lot, and further leads to serious water scarcity (Xie et al., 2021). It is also suspected of causing cancer, congenital impairments, immune and reproductive system dysfunction, and endangering the growth of newborns and children (Ahmed & Haider, 2018; Gusain et al., 2019; Nadimi et al., 2019).



Creative Commons Non Commercial CC BY-NC: This article is distributed under the terms of the Creative Commons Attribution-NonCommercial 4.0 License (<https://creativecommons.org/licenses/by-nc/4.0/>) which permits non-commercial use, reproduction and distribution of the work without further permission provided the original work is attributed as specified on the SAGE and Open Access pages (<https://us.sagepub.com/en-us/nam/open-access-at-sage>).

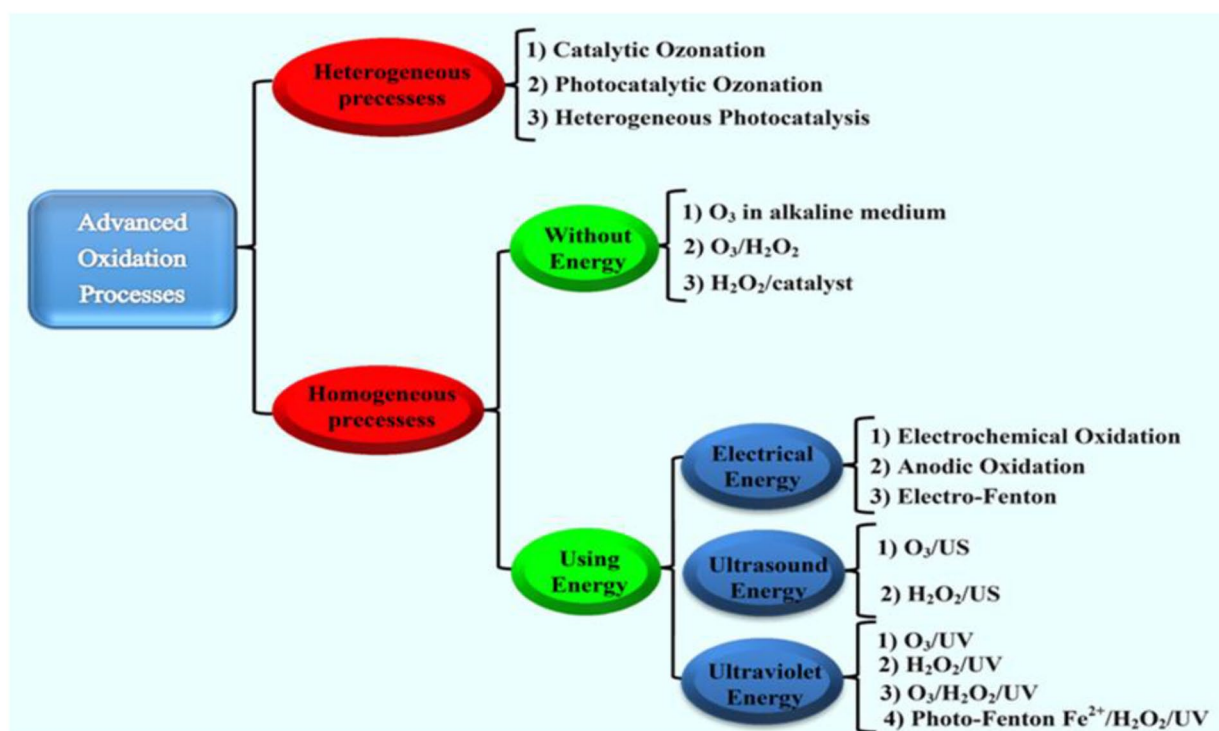


Figure 1. Various classifications of advanced oxidation process (Mousavi et al., 2018).

Among major categories of organic pollutants, modern commercial dyes are characterized by strong structural and color stability due to their high degree of aromaticity and extensively conjugated chromophores. These dyes are widely utilized in a variety of industries, including printing, leather, cosmetics, plastics, food, and, most notably, textiles, and their unintentional release into the environment poses a risk to human health and ecological systems. Furthermore, these toxic and carcinogenic synthetic colors would prevent sunlight from entering water bodies, harming natural aquatic activities including photosynthesis and other biodegradation processes. These toxins will endanger human health and the environment if they are not effectively removed (Cheng et al., 2013).

Water is the most precious resource that should be conserved, treated, and recycled scientifically for sustainable use in every aspect of life (Sudhaik et al., 2018). Therefore, various conventional approaches have been practiced for wastewater treatment such as coagulation, flocculation, filtration and membrane separation, sedimentation, reverse osmosis, adsorption, disinfection and advanced oxidation, and biological methods (Ghafoor et al., 2019; Kumar & Chowdhury, 2020; Miklos et al., 2018). However, the efficiency of these remedial techniques is limited for the purification of wastewater containing persistent organic pollutants (Iervolino et al., 2019; Sudhaik et al., 2018). Moreover, various conventional approaches are ineffective, time-consuming, chemically intensive, and have reached a significant level of maturity (Dewil et al., 2017; Kumar, Khan, et al., 2018).

For the removal of diverse contaminants from industrial wastewater, efficient wastewater treatment techniques should be utilized (Varma et al., 2020). As a result, Advanced Oxidation

Processes (AOPs) are a series of chemical treatment procedures that use oxidation to mineralize organic contaminants, water pathogens, and disinfection byproducts by the in-situ production of highly reactive species (Babuponnusami & Muthukumar, 2014; Malato et al., 2009). It works by producing highly reactive chemical species such as hydroxyl radicals ($\cdot\text{OH}$) and superoxide anion radicals ($\cdot\text{O}_2^-$) that attack organic contaminants. The efficiency of AOPs is based on the generation of these highly reactive radicals, which are unselective and robust oxidizing species ($E^\circ = 2.80\text{ V}$) capable of degrading micropollutants with reaction rate constants typically around 10^6 to $10^9\text{ mol L}^{-1}\text{s}^{-1}$, yielding CO_2 , H_2O , and, eventually, inorganic ions as final products (Ribeiro et al., 2015; Saravanan et al., 2017).

The classification of AOPs is very difficult due to the multiple processes involved. However, it can be classified as homogeneous or heterogeneous processes depending on the phase of the catalyst used (Figure 1). Despite their use in wastewater treatment, these processes have several limitations, including the need for complex equipment, ozone's short half-life, UV radiation absorption, partial mineralization of contaminants, and high costs of these processes (Sudhaik et al., 2018).

Furthermore, most AOPs require the use of additional chemicals as oxidants and energy which aggravates the energy crisis (Zhang, Gu, et al., 2019). Except for semiconductor-based Photocatalysis, the remaining advanced oxidation process have practical limitations, such as H_2O_2 transport and storage, cost-intensive oxidant synthesis, and sludge generation (Yao et al., 2014). Among the possible AOPs techniques for wastewater treatment, semiconductor-based photocatalysis has been known as a green, simple, and cost-effective technique for the complete

degradation of organic contaminants in wastewater (Gusain et al., 2020; Ismael et al., 2020). Moreover, It is by far one of the most superior and promising environmental purification technologies, not only because it uses the most plentiful solar energy and molecular oxygen (as an oxidant species), but also because it degrades persistent hazardous contaminants to carbon dioxide, water, and inorganic minerals (Dong et al., 2017; Sun et al., 2018).

The best solution for energy production and the elimination of pollutants is to use solar energy, which is a powerful, affordable, and renewable energy source (Low, Jiang, et al., 2017). Therefore, the use of sunlight is both cost-effective and environmentally friendly as well as minimizes chemicals to be used and toxic emissions in the environment for various applications (Raja & Jaffar Ali, 2021). Solar energy reaching the Earth's surface is dominated by three regions of the electromagnetic spectrum namely UV (~5%), visible (~45%), and IR (~50%) (Kumar, Karthikeyan, et al., 2018). However, the challenge here is to identify suitable photocatalytic materials capable of capturing photons, particularly those in the visible light spectrum. The search for visible light-active photocatalysts is a hot topic nowadays (Zhu et al., 2014). Therefore, the formation of heterostructured composite is desirable to utilize the extended sunlight radiation for photocatalytic applications of environmental remediation (Raja & Jaffar Ali, 2021). Moreover, constructing a heterostructured composite can greatly promote the separation of photo-generated charge carriers and the photocatalytic activity of the catalyst. The excellent photocatalytic performance of the $g\text{-C}_3\text{N}_4/\text{TiO}_2$ heterojunction catalysts makes them promising candidates for environmental remediation (Zhou et al., 2017). Meanwhile, $g\text{-C}_3\text{N}_4$ can form the heterojunction with TiO_2 to reduce the recombination of photogenerated electron-hole pairs and significantly enhance the photocatalytic activity of TiO_2 under visible light due to the close interfacial connection and appropriate conduction and valence band levels (Li et al., 2016). Due to such merits, different heterostructures of $g\text{-C}_3\text{N}_4/\text{TiO}_2$ nanocomposite photocatalysts have been prepared for the photodegradation of dyes in wastewater. For instance, Li et al. synthesized $g\text{-C}_3\text{N}_4/\text{TiO}_2$ hybrid photocatalysts through a modified sol-gel technique. Compared with pure $g\text{-C}_3\text{N}_4$ and TiO_2 , the $g\text{-C}_3\text{N}_4/\text{TiO}_2$ heterojunction photocatalysts exhibited enhanced visible-light photoactivity, which is around 3.5 times as high as that of the pure $g\text{-C}_3\text{N}_4$ and eight times as much as the pure TiO_2 . The appropriate band gap, the heterojunction between $g\text{-C}_3\text{N}_4/\text{TiO}_2$, and the substantially greater surface area are all factors that contribute to the high photocatalytic activity of the $g\text{-C}_3\text{N}_4/\text{TiO}_2$ composite. In addition, the photocatalytic performance of the $g\text{-C}_3\text{N}_4/\text{TiO}_2$ hybrid photocatalysts was stable, indicating that it is a promising material for dye photodegradation in wastewater (Li et al., 2016). Hao et al. fabricated $g\text{-C}_3\text{N}_4/\text{TiO}_2$ heterojunction composites via in situ hydrothermal synthesis followed by calcination method. Compared with pure $g\text{-C}_3\text{N}_4$ and TiO_2 , the $g\text{-C}_3\text{N}_4/\text{TiO}_2$ heterojunction composites exhibited higher photocatalytic

performance for decomposition of Rhodamine B (RhB), which is around 3.5 times as high as that of the pure $g\text{-C}_3\text{N}_4$ and 18.5 times as much as the pure TiO_2 . The high activity can be ascribed to the high specific surface area of the $g\text{-C}_3\text{N}_4/\text{TiO}_2$ composites and a synergistic heterojunction structure between TiO_2 and $g\text{-C}_3\text{N}_4$ (Hao et al., 2017).

Many recent reports are not available on recent advances in $g\text{-C}_3\text{N}_4/\text{TiO}_2$ -based nanocomposite photocatalysts for wastewater treatment. Therefore, these factors triggered the interest in this research in the near future. Herein this review will mainly focus on the recent developments and ways of boosting the photocatalytic activity of $g\text{-C}_3\text{N}_4/\text{TiO}_2$ -based nanocomposite photocatalysts for organic pollutant degradation. Meanwhile, this critical review provides academic insight into strategies for improving charge separation and transfer efficiency, broadening visible light absorption, improving photoinduced charge carrier mobility, increasing surface area and active sites, and improving photocatalytic activity of $g\text{-C}_3\text{N}_4/\text{TiO}_2$ -based heterostructured nanocomposites. It also pinpoints strategies for boosting the photocatalytic performance of $g\text{-C}_3\text{N}_4/\text{TiO}_2$ -based heterojunction composites for practical application in environmental remediation. Finally, we will give a summary and outlook on constructing different types of $g\text{-C}_3\text{N}_4/\text{TiO}_2$ -based heterostructure nanocomposite photocatalysts.

Basic Principles and Mechanism of Heterogeneous Photocatalysis

The accepted definition of photocatalysis, according to the glossary of terms and conditions used during photocatalysis, consists of a change in the rate of chemical reaction in the presence of an absorber of light by a photocatalyst in the presence of ultraviolet, visible, or infrared radiation and the photocatalyst is defined as a substance which, by absorption of ultraviolet, visible or infrared radiation, can repeatedly produce a chemical transformation of reaction partners into intermediate chemical interactions and regenerate their chemical composition after each interaction cycle (Augugliaro et al., 2019).

Among the several known advanced oxidation technologies, semiconductor-based heterogeneous photocatalysis is the most effective method for degrading contaminants without producing harmful intermediates at ambient pressure and temperature (Basavarajappa et al., 2020). In a photocatalytic process, electrons could be excited from the valence band (VB) to the conduction band (CB) of a photocatalyst, when exposed to light with energy that is greater than or equal to the bandgap energy of a photocatalyst (Sudhaik et al., 2018). Holes can directly oxidize pollutants or react with $\text{H}_2\text{O}/\text{OH}^-$ to produce hydroxyl radicals ($\cdot\text{OH}/\text{H}_2\text{O} = 2.8\text{ eV/NHE}$). Whereas the electrons capture dissolved oxygen (O_2) to yield superoxide radical ($\text{O}_2/\cdot\text{O}_2^- = -0.3\text{ eV/NHE}$) (Shen et al., 2020). Moreover, the generation of $\cdot\text{OH}$ radicals are normally concerned with two routes, (i) H_2O and OH^- in the water environment can be readily oxidized by photogenerated h^+ to form $\cdot\text{OH}$ radicals; (ii) O_2 presented in the aqueous solution can be reduced by

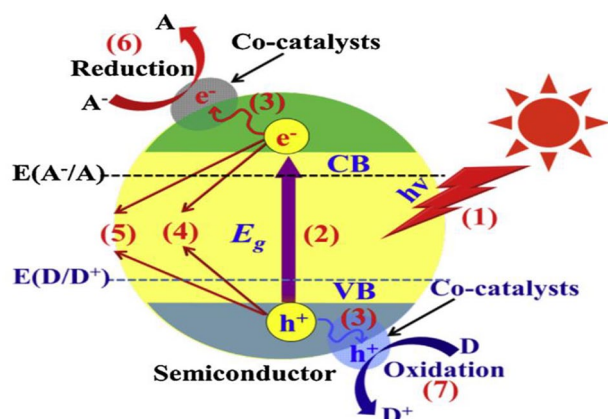


Figure 2. Schematic illustrations of major photocatalytic processes (Prasad et al., 2019).

photogenerated e^- form $\cdot\text{O}_2^-$ radicals, followed by reacting with h^+ (forming $\cdot\text{OOH}$ radicals) and further decomposition to produce $\cdot\text{OH}$ radicals (Dong et al., 2015; Huang et al., 2019; Muhd Julkapli et al., 2014). Under appropriate conditions, photocatalysis generates reactive oxygen species (ROS) like; $\cdot\text{OH}$, $\cdot\text{O}_2^-$, $^1\text{O}_2$, H_2O_2 , and holes (h^+) which can facilitate the degradation of pollutants (Kumar, Raizada, et al., 2020).

Finally, Photo-generated electron-hole pairs migrate to the surface of the photocatalyst to participate in redox reactions to degrade pollutants (Sudhaik et al., 2018). Moreover, with the irradiation of UV or visible light with energy larger than or equal to the semiconductor's energy bandgap, the electron-donating, and electron-accepting sites are formed inside the surface of the semiconducting catalyst (Shen et al., 2020). However, if the photo-generated electrons and holes are not scavenged immediately after photoexcitation, they may recombine on the surface or in the bulk of the semiconductor, releasing the absorbed energy as heat or light (Huang et al., 2019; Muhd Julkapli et al., 2014).

In general, each photocatalytic reaction involves seven key steps which can be categorized into four main stages: light absorption through the semiconductor to generate pairs of electron-hole (stage 1); charge excitation (stage 2); charge separation and migration to the semiconductive surface or bulk recombination (stages 3, 4, and 5); and surface redox reactions (stages 6 and 7). These four steps are mutually exclusive, and the thermodynamics and kinetics of these processes determine the efficiency of the photocatalyst (Figure 2) (Wen et al., 2017).

Moreover, the overall photocatalyst efficiency has been significantly affected by the combined effects of four-stage processes such as (a) light absorption, (b) charge separation efficiency, (c) charge migration and transportation efficiency, and (d) charge usage efficiency. The overall efficiency of the various photocatalytic processes can be described as follows:

$$\eta_c = \eta_{abs} \times \eta_{cs} \times \eta_{cmt} \times \eta_{cu} \quad (1)$$

Where η_c is the solar energy conversion efficiency, η_{abs} is the light absorption efficiency, η_{cs} is the charge excitation/separation efficiency, η_{cmt} is the charge migration and transportation

efficiency, and η_{cu} is the charge usage efficiency for photocatalysis reactions. Therefore, all of these typical four-step processes must be fully considered and optimized to design highly efficient visible-light-driven photocatalysts for organic pollutant degradation (Wen et al., 2015, 2017).

Structure and Photocatalytic Properties TiO_2 Photocatalysts

Among all semiconductor photocatalysts, TiO_2 is receiving tremendous attention as a promising photocatalyst for environmental remediation due to its intriguing photocatalytic properties such as higher redox potential, high reactivity, higher efficiency, robust chemical stability, non-toxicity, ease of preparation, and cost-effective (Peiris et al., 2021; Tsang et al., 2019). It exists commonly in three crystalline phases such as anatase, rutile, and brookite (Figure 3) (Jianmin & Informatio, 2016; Pelaez et al., 2012). The dominant faces in the morphology of crystalline anatase are (011) and (001). The (001) face is highly reactive and it affects the catalytic activity, stability, and absorptive properties (Peiris et al., 2021). Moreover, anatase and rutile are the most commonly used in photocatalytic applications, although anatase is considered to be more photoactive than rutile, because of its stronger reducing power and better hole-trapping ability (Gopalan et al., 2020; Tobaldi et al., 2013). Among these three polymorphs, rutile is the most stable whereas anatase and brookite are metastable phases (Singh & Dutta, 2018). Therefore, the brookite and anatase polymorphs will change into the thermodynamically stable rutile polymorph when calcined at high temperatures exceeding 600°C (Jianmin & Informatio, 2016; Pelaez et al., 2012). Brookite is generally more reactive than anatase. However, preparing pure brookite without rutile or anatase is rather difficult, and therefore it has not been widely investigated (Di Paola et al., 2013). Other than pure anatase TiO_2 products, some commercial TiO_2 products contain pure anatase or a mixture of 25% rutile and 75% anatase with a bandgap in the range of 3.15 to 3.21 eV (Tsang et al., 2019). The overlapping of 2p orbitals of oxygen forms a valance band (VB) in these crystalline phases, whereas the 3d orbitals of Ti^{4+} are responsible for the formation of the lower half of the conduction band (CB) (Daghrir et al., 2013). Anatase crystal structure comes from corner-sharing of the octahedral which forms (001) planes resulting in the tetragonal structure; whereas the rutile crystal structure comes from the edge-sharing of (001) planes of octahedral which gives a tetragonal structure (Pelaez et al., 2012). In the case of brookite, both the edge and corner-sharing provide an orthorhombic structure (Chen & Mao, 2007). The Ti-Ti distances in anatase are longer than the Ti-O distance, which results in differences in their electronic band structures (Burdett et al., 1987). Rutile has a higher density than anatase, and these structural differences result in differences in photocatalytic activity (Gupta & Tripathi, 2011; Nolan et al., 2010).

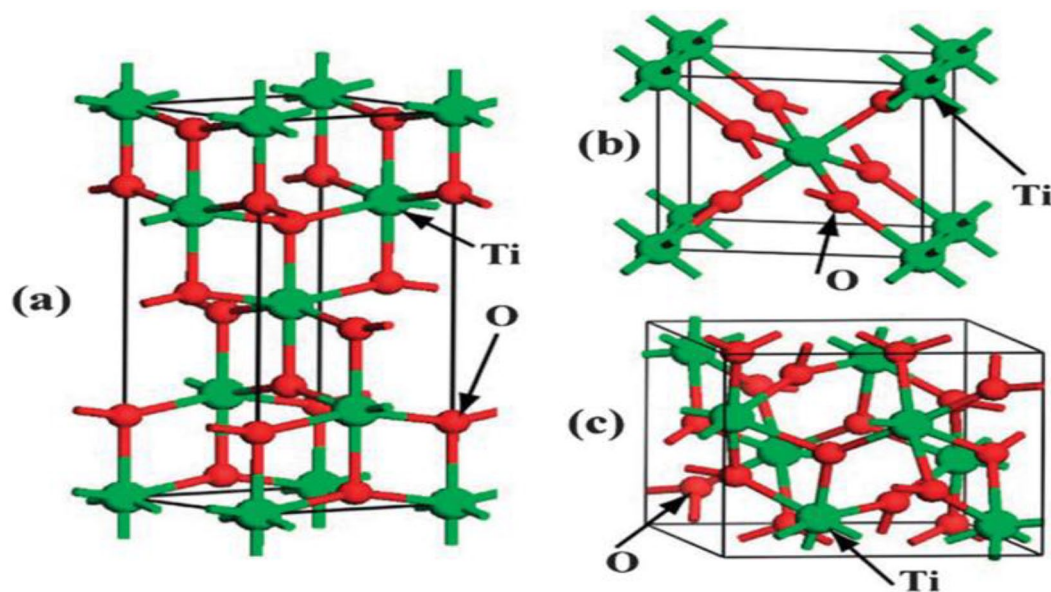


Figure 3. Crystal structure of TiO_2 polymorphs: (a) anatase, (b) rutile, and (c) brookite (Zhang et al., 2014).

Strategies for improving TiO_2 photoactivity

The modification of TiO_2 to overcome the limitations in the use of pure TiO_2 is one of the most widely studied topics in the field of photocatalysis. In recent years, some of the major approaches have been proposed to boost the photocatalytic activity of TiO_2 such as elemental doping, constructing heterojunctions with other small bandgap semiconductors, noble metal deposition, and dye sensitization (Li et al., 2020).

Doping of metal and nonmetal elements. The most significant factor that hindered the practical application of TiO_2 is the fast recombination of photoinduced electron-hole pairs and poor photosensitivity of TiO_2 under visible light irradiation. In general, ordinary TiO_2 has a wide intrinsic band gap (3.2 eV for anatase and 3.0 eV for rutile), allowing it to absorb only UV light, which accounts for just 5% of the sunlight (Li et al., 2020). Therefore, absorption of only ultraviolet radiation limits the use of all the energy of sunlight to activate photocatalytic processes (Salomatina et al., 2021). The visible light absorption of TiO_2 can be enhanced through metal and non-metal doping of the photocatalyst (Nasirian et al., 2018). Moreover, Doping causes the production of vacancies such as interstitial or substitutional defects which alter the color, conductivity, reactivity, and optical and magnetic properties of doped oxides (Rahimi et al., 2016). Enhancing the photocatalytic activity of TiO_2 by doping metals or non-metal ions has been presented in recent reviews (Basavarajappa et al., 2020; Tsang et al., 2019; Varma et al., 2020; Wen et al., 2015; Yadav & Jaiswar, 2017).

Constructing heterojunctions. The photocatalytic efficiency of TiO_2 may be significantly improved by combining it with other small bandgap semiconductors to produce a heterojunction. This approach may not only enhance the separation of photo-generated electron-hole pairs, but it can also extend the spectral response range to visible light and even the near-infrared region

(Li et al., 2020). The main design considerations of heterostructures are focused on extending light absorption, increasing specific surface area, introducing cocatalyst to reduce the overpotential of catalytic reaction, and improving the separation of photogenerated electron-hole pairs. Therefore, the design of heterojunction nanocomposites has become a compelling and feasible approach to overcoming the limitations of pristine TiO_2 in terms of photocatalytic activity (Fu et al., 2018; Low, Yu et al., 2017; Ong et al., 2016).

In particular, coupling TiO_2 with graphitic carbon nitride ($\text{g-C}_3\text{N}_4$) represents an intriguing solution to enhance the photocatalytic activities of TiO_2 . Additionally, the delocalized conjugated structure of $\text{g-C}_3\text{N}_4$ gives rise to a slow charge recombination rate and promotes photoinduced charge carriers separation and transportation. In contrast, the formation of a charge-transfer complex at the interface between $\text{g-C}_3\text{N}_4$ and TiO_2 results in a $\text{g-C}_3\text{N}_4/\text{TiO}_2$ heterojunction that shows a decrease in the recombination rate of photogenerated electron-hole pairs as well as an increase in the photocatalytic activity of TiO_2 under visible light irradiation (Porcu et al., 2020; Zhou et al., 2017). There have been excellent reviews on heterojunction-based photocatalysts for the degradation of persistent organic pollutants and readers can refer to these review articles (Low, Yu, et al., 2017; Xie et al., 2021).

Various types of $\text{g-C}_3\text{N}_4/\text{TiO}_2$ -based nanocomposite heterojunctions for organic pollutant degradation in wastewater are presented in detail in this review. Meanwhile, Tables 1 to 3 sum up the latest reports on different types of $\text{g-C}_3\text{N}_4/\text{TiO}_2$ -based nanocomposite heterojunctions for photodegradation of organic pollutants in wastewater.

Noble-metals deposition. The deposition of a noble metal on semiconductor nanoparticles is an important factor in improving the efficiency of photocatalytic reactions. Subsequently, it

Table 1. Recent Developments on the Photocatalytic Application of g-C₃N₄/TiO₂-Based Type-II Heterojunction Nanocomposites for the Degradation of Organic Pollutants.

| PHOTOCATALYST | SYNTHESIS METHOD | LIGHT SOURCE (CUTOFF FILTER) | POLLUTANT CONCENTRATION | REACTION TIME | DEGRADATION EFFICIENCY (%) | REFERENCE |
|--|---------------------------------|--|-------------------------|------------------|----------------------------|-------------------------------------|
| g-C ₃ N ₄ -C/N-TiO ₂ | Thermal transformation | 100 W Halogen lamp ($\lambda > 400$ nm) | MB: 15 μ M | 100 minutes | 93 | Sridharan et al. (2013) |
| N-TiO ₂ /g-C ₃ N ₄ | Microwave assisted | 300 W Xe lamp ($\lambda > 400$ nm) | Rh B/MB: 10 mg/L | 60 minutes | 77/69 | Wang et al. (2013) |
| g-C ₃ N ₄ NSs/N-TiO ₂ NFs | Electrospinning/heat etching | Simulated solar light | Rh B: 10 ppm | 300 minutes | 100 | Han et al. (2015) |
| g-C ₃ N ₄ /TiO ₂ | Hydrothermal | 300-W Xe lamp ($\lambda > 400$ nm) | MO: 100 μ M | 300 minutes | 40 | Mohini and Lakshminarasimhan (2016) |
| g-C ₃ N ₄ /TiO ₂ | Sol-gel | 500 W Xe lamp ($\lambda > 400$ nm) | MB: 10 mg/L | 360 minutes | 90 | Li et al. (2016) |
| g-C ₃ N ₄ -TiO ₂ -GA | Hydrothermal/freeze-drying | 500 W Xe lamp ($\lambda > 400$ nm) | RhB: 20 mg/L | 60 minutes | 98 | Zhang et al. (2018) |
| C-TiO ₂ /g-C ₃ N ₄ | Hydrothermal | 300 W Xe lamp ($\lambda > 400$ nm) | MO: 20 mg/L | 60 minutes | 99 | Lu et al. (2017) |
| g-C ₃ N ₄ /TiO ₂ NTs | Hydrothermal/calcination | 450 W Xe lamp ($\lambda > 400$ nm) | SMT: 5 mg/L | 300 minutes | 100 | Ji et al. (2020) |
| g-C ₃ N ₄ /TiO ₂ NTs | Chemical vapor deposition | 300 W Xe lamp ($\lambda > 400$ nm) | RhB: 5 mg/L | 150 minutes | 99 | Liu, Bie, et al. (2019) |
| D35-TiO ₂ /g-C ₃ N ₄ | Hydrothermal | 300 W Xe lamp ($\lambda > 400$ nm) | BPA: 10 mg/L | 15 minutes | 100 | Yang et al. (2019) |
| g-C ₃ N ₄ -TiO ₂ | Hydrothermal | Sunlight irradiation | BG/BPA: 20 mg/L | 150 /240 minutes | 95/88 | Sutar et al. (2020) |
| g-C ₃ N ₄ -TiO ₂ | Hydrothermal | 300 W Xe lamp Without UV filter | MB: 10 mg | 180 minutes | 80 | Gündoğmuş et al. (2020), |
| GQDs/Mn-N-TiO ₂ /g-C ₃ N ₄ | Hydrothermal | 300 W Xe lamp (320 $\leq \lambda \leq$ 780 nm) | 4-NP/CIP/DEP : 10 mg/L | 120 minutes | 89/70/ 49 | Nie et al. (2018) |
| g-C ₃ N ₄ /TiO ₂ /Kaolinite | Mild sol-gel/chemical stripping | Xe lamp ($\lambda > 400$ nm) | CIP: 10 mg/L | 240 minutes | 92 | Li, Sun, et al. (2018) |

Note. DE = degradation efficiency; NSs = nanosheets; NTs = nanotubes; D35 = D35 dye; NFs = nanofibers; MB = methylene blue; MO = methyl orange; Rh B = rhodamine B; SMT = Sulfamethazine; BPA = bisphenol A; BG = brilliant green; CIP = ciprofloxacin; GQDs = Graphene quantum dots; GA = graphene aerogel.

Table 2. Summary of All-Solid-State Indirect Z-Scheme g-C₃N₄-TiO₂ Based Heterojunction Nanocomposites for Degradation of Organic Pollutants in Wastewater.

| PHOTOCATALYST | SYNTHESIS METHOD | LIGHT SOURCE (CUTOFF FILTER) | POLLUTANT CONCENTRATION | REACTION TIME | DEGRADATION EFFICIENCY (%) | REFERENCE |
|---|--------------------------------------|--|-------------------------|---------------|----------------------------|--------------------------|
| g-C ₃ N ₄ /TiO ₂ NTAs | Immersing/calcination | 300W Xe lamp ($\lambda \geq 420\text{nm}$) | Rh B: 5 mg/L | 5 hours | 67 | Zhou, Chen et al. (2016) |
| g-C ₃ N ₄ NSs/TiO ₂ NTAs | Simple dispersing/anodization | 300W Xe lamp ($\lambda \geq 420\text{nm}$) | Rh B: 5 mg/L | 5 hours | 76 | Zhou, Chen et al. (2016) |
| g-C ₃ N ₄ -RGO-TiO ₂ | liquid-precipitation | 300W Xe lamp ($\lambda \geq 420\text{nm}$) | MB: 30 mg/L | 3 hours | 92 | Wu et al. (2017) |
| TiO ₂ NPs-Fe-C ₃ N ₄ NSs | Grafting-calcination | N/A | MO:10 mg/L | 1 hour | 89 | Xu et al. (2019) |
| g-C ₃ N ₄ /Pd/TiO ₂ | Photo-deposition/calcination process | 300W Xe lamp ($\lambda \geq 420\text{nm}$) | Propylene: 0.5 mmol/L | 13 minutes | 34 | Guo et al. (2018) |
| g-C ₃ N ₄ /TiO ₂ | Sol-gel/spin coating | 300W Xe lamp ($\lambda \geq 420\text{nm}$) | RhB/TC-HCl: 5 mg/L | 3 hours | 31/26 | Zhao et al. (2020) |

Note. NTAs = nanotube arrays; NSs = nanosheets; Rh B = rhodamine B; MB = methylene blue; TC-HCl = tetracycline hydrochloride; DE = degradation efficiency.

is commonly assumed that the noble metal acts as a sink for photo-generated charge carriers and promotes interfacial charge transfer (Rahimi et al., 2016). Noble-metal nanoparticles (NPs) such as Au and Ag can respond to visible light due to the localized surface plasmon resonance (LSPR), which is the result of the collective oscillations of the surface electrons, exhibiting great potential for extending the light absorption range of wide band gap semiconductors (Lu et al., 2012). Fermi levels of these noble metals are lower than that of TiO₂, which results in the effective transfer of the photoinduced electrons from the conduction band of TiO₂ to metal particles. This electron trapping process inhibits the electron-hole recombination rate, which results in stronger photocatalytic reactions (Etacheri et al., 2015). Recently, an excellent review article has been carried out on the recent progress of noble metals with tailored features in catalytic oxidation for organic pollutants degradation (Fu et al., 2022). For instance, Moslah et al. used a sol-gel/spin-coating method for preparing nanocrystalline pure and noble metal (Ag, Au, Pd, and Pt)-doped TiO₂ thin films. The order of photocatalytic activity is most probably related to the work function order, Pt-TiO₂ > Pd-TiO₂ > Au-TiO₂ > Ag-TiO₂ > pure TiO₂ (Moslah et al., 2018).

Dye-sensitization. An intriguing strategy for achieving effective visible light-harvesting is the photosensitization of wide-band-gap semiconductors by appropriate sensitizer molecules (Dong et al., 2015). During visible-light irradiation, excited electrons are transferred from the dyes to the conduction band of the semiconductor (Etacheri et al., 2015). Meanwhile, several electron transfer steps are involved in this process. The physical adsorption of dyes occurs through the weak van der Waals interaction between the dye molecule and the TiO₂ surface. The photochemical process is initiated by photoexcitation of dye molecules upon irradiation by visible light, followed by the transfer of the electrons from the excited dye to the conduction band of TiO₂ (see Figure 4). Subsequently, in the presence of suitable electron donors (eg, EDTA, organic acids, water, alcohols, etc.), the oxidized dye is regenerated. The injection of an electron into the conduction band of TiO₂ is favorable due to the more negative potential of the lowest unoccupied molecular orbital (LUMO) of the dye molecules as compared to the potential of the TiO₂ conduction band (Daghrir et al., 2013; Rehman et al., 2009). Some dyes are even capable of producing electrons by absorbing visible light in the absence of semiconductors. Nevertheless, in the absence of semiconductor charge separators, photocatalytic activities of these dyes are too low. Visible-light absorption and electron transfer to the conduction band of TiO₂ often resulted in a superior photocatalytic activity (Etacheri et al., 2015). Generally, various researchers conducted a comprehensive review of different modification strategies to enhance the photocatalytic activity of TiO₂ (Humayun et al., 2018; Li et al., 2020; Wen et al., 2015).

Table 3. Summary of Recent Developments in Direct Z-Scheme g-C₃N₄/TiO₂ Heterojunction Nanocomposites for Organic Pollutant Degradation.

| PHOTOCATALYST | SYNTHESIS METHOD | LIGHT SOURCE (CUTOFF FILTER) | POLLUTANT CONCENTRATION | REACTION TIME | DEGRADATION EFFICIENCY | REFERENCE |
|---|------------------------------|-------------------------------|-------------------------|---------------|------------------------|----------------------------|
| g-C ₃ N ₄ -TiO ₂ NTs/Nps | Wetness impregnation | N/A | Isoniazid: 50 mg/L | 240 minutes | 91 | Jo and Natarajan (2015) |
| g-C ₃ N ₄ /TiO ₂ -HNB | Solvothermal | 3 W LED UV (355 ≤ λ ≤ 375 nm) | X3B: 0.1 mmol/L | 45 minutes | 100 | Huang et al. (2015) |
| CN QDs- rTiO ₂ | Calcination | 500 W Xe lamp | RhB: 5 mg/L | 300 minutes | 95 | Li, Lv, et al., (2017) |
| g-C ₃ N ₄ /TiO ₂ | Calcination | 300 W Xe lamp (λ ≥ 420 nm) | Propylene | 60 minutes | 57 | Li, Zhang, et al., (2017) |
| g-C ₃ N ₄ -N-TiO ₂ | Simple calcination | 350 W Xe lamp (λ ≥ 420 nm) | RhB: 10 μM | 80 minutes | 96 | Lu et al. (2018) |
| g-C ₃ N ₄ -TiO ₂ | Solvothermal | 65 W visible light | RhB: 5 ppm | 80 minutes | 97 | Monga and Basu (2019) |
| g-C ₃ N ₄ -TiO ₂ | Hydrothermal/ion-exchange | 300 W Xe lamp (λ ≥ 420 nm) | RhB: 10 mg/L | 30 minutes | 90 | Liu, Wei, et al. (2020) |
| O-g-C ₃ N ₄ @Fe-TiO ₂ | Fragment coating | 300 W Xe lamp (λ > 380 nm) | MB: 20 mg/L | 60 minutes | 100 | Wang and Liu (2019) |
| g-C ₃ N ₄ -TiO ₂ | Solvothermal | 500 W Xe lamp | RhB: 10 mg/L | 10 minutes | 100 | Zhang, Li, et al. (2019) |
| g-C ₃ N ₄ -TiO ₂ | Solvothermal | 20 W UV-Vis | Acid orange 7 : 5 mg/L | 12 minutes | 100 | Liu, Li, et al. (2020) |
| g-C ₃ N ₄ -TiO ₂ | Impregnation | 300 W Xe lamp (λ ≥ 420 nm) | Rh B: 5 mg/L | 300 minutes | 45 | Zhou et al. (2020) |
| TiO ₂ /g-C ₃ N ₄ /RGO | Electrospinning/annealing | 500-W Xe lamp | RhB: 10 mg/L | 60 minutes | 99 | Hu et al. (2019) |
| g-C ₃ N ₄ /TiO ₂ NTs | Anodic oxidation/calcination | 250 W Hg lamp (λ ≥ 420 nm) | RhB: 15 mg/L | 160 minutes | 96 | Bi et al. (2020) |
| CDs/TiO ₂ /g-C ₃ N ₄ | Hydrothermal | 350 W Xe lamp (λ ≥ 420 nm) | ENX: 4 mg/L | 60 minutes | 92 | Su et al. (2017) |
| g-C ₃ N ₄ /TiO ₂ /Fe ₃ O ₄ @SiO ₂ | Sol-gel | 64 W fluorescent lamp | Ibuprofen: 2 mg/L | 60 minutes | 98 | Kumar, Khan, et al. (2018) |

Note. DE = degradation efficiency; NTs = nanotubes; NPs = nanoparticles; HNB = hollow nanobox; QDs = quantum dots; RGO = reduced graphene oxide; Rh B= rhodamine B; MB = methylene blue; X3B = Brilliant Red X-3B dye; THCL = Tetracycline hydrochloride; ENX=enrofloxacin.

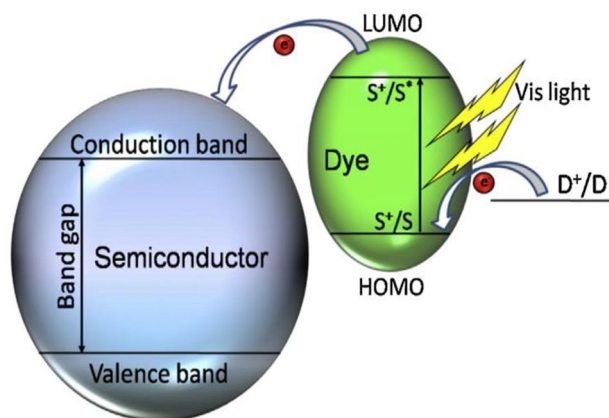


Figure 4. Mechanism of dye-sensitized semiconductor photocatalysis (Etacheri et al., 2015).

Properties, Preparation Strategies, and Photocatalytic Applications of g-C₃N₄

Origin and synthesis of g-C₃N₄

Graphitic carbon nitride (g-C₃N₄), a metal-free polymeric material containing carbon and nitrogen, the two earth-abundant elements, has exhibited excellent photocatalytic performance. Its exceptionally tunable and stable physical and chemical properties, distinctive electronic band structure along with facile synthesis makes it a unique photocatalytic material (Kumar, Raizada, et al., 2020).

Since Wang et al. first reported in 2009 on using graphitic carbon nitride as a metal-free conjugated semiconductor photocatalyst for hydrogen production, it has been regarded as a promising material for photocatalytic applications (Wang, Maeda et al., 2009). g-C₃N₄ contains seven different phases predicted by calculations of the first principle such as alpha-C₃N₄, beta-C₃N₄, pseudocubic C₃N₄, g-h-triazine, g-h-heptazine, and g-o-triazine with 5.49, 4.85, 4.30, 4.30, 2.97, 2.88, and 0.93 eV band gaps, respectively (Prasad et al., 2019; Sudhaik et al., 2018; Wen et al., 2017; Xu, Ahmed et al., 2018). A similar hardness and low compressibility to the diamond phases is the famous super hard phase β -C₃N₄ crystalline. It is also structured in the same way as Si₃N₄, replacing the silicon atom with a carbon atom. Meanwhile, because alpha-C₃N₄ is comprised of layers of beta-C₃N₄ alternating with its mirror image stack, it shares many of the same properties as beta-C₃N₄, such as crystalline structure, and bulk modulus, and atomic density (Wang et al., 2015). The remaining five phases except for the pseudocubic C₃N₄ and g-h-triazine phases have indirect band gaps in their bulk structures. With band gaps of 2.97 and 2.88 eV, the g-h-triazine and g-h heptazine phases are appropriate for a variety of visible-light active photocatalytic applications (Wen et al., 2017).

Triazine rings (C₃N₃) as tectonic units and tri-s-triazine (heptazine) ring as central units are the two fundamental building blocks of g-C₃N₄ materials. The polymer melon hypothesis is linked to tri-s-triazine, which is the most stable pattern,

energetically favored, and widely accepted structural unit (Figure 5) (Mousavi et al., 2018).

Properties and preparation of g-C₃N₄ photocatalyst

Thermogravimetric analysis shows that g-C₃N₄ is thermally stable in the air up to 600°C. It became unstable and the skeleton becomes collapsed over 600°C, and then it was completely decomposed into small CO₂ and NH₃ molecules beyond 700°C (Chen et al., 2020). Furthermore, g-C₃N₄ is chemically stable and does not dissolve in acid, alkali, or organic solvents, making it a robust material under normal conditions (Ong et al., 2016). g-C₃N₄ is not only the most stable carbon allotrope in the ambient atmosphere but also has rich surface properties which are attractive for catalysis applications due to the presence of primary surface sites (Zhu et al., 2014).

The attractive electronic structure, non-toxic, low density, earth-abundant nature, and moderate bandgap of 2.7 eV of g-C₃N₄ make it a good choice for visible light-assisted photocatalytic water purification. Furthermore, perfectly condensed g-C₃N₄ has only two earth-abundant elements: C and N, with a C/N molar ratio of 0.75, implying that g-C₃N₄ might be synthesized cheaply. Graphitic carbon nitride (g-C₃N₄) is distinguished from graphene and other analogs by its semiconductor character. Furthermore, g-C₃N₄ in nanocomposites is being investigated as a possible photocatalyst for photocatalytic organic pollutant degradation in wastewater (Sudhaik et al., 2018; Wen et al., 2017).

Pure g-C₃N₄ has a conduction band potential of around 1.3 V (normal hydrogen electrode (NHE) at pH = 7), which is more negative than the potential of photocatalytic reduction of carbon dioxide (CO₂) into hydrocarbons like methane (CH₄) (-0.24 V), methanol (CH₃OH) (-0.38 V), formaldehyde (HCHO) (-0.48 V), ethanol (CH₃CH₂OH) (-0.33 V), and formic acid (HCOOH) (-0.61 V). It's also lower than the potential for H₂ evolution, which stands at -0.41 V (NHE at pH 7). Pure g-C₃N₄ has a valence band position of +1.4 V (NHE at pH 7), which is higher than the water oxidation potential. As a result, g-C₃N₄ can be used in photocatalytic CO₂ reduction, photocatalytic water splitting, and degradation of organic pollutants (Wang et al., 2015).

Thermal polymerization, solvothermal, chemical vapor deposition, and electrochemical deposition are some of the chemical methods used to synthesize g-C₃N₄. The thermal polycondensation method, on the other hand, is universally used in a wide range of reported research due to its simple and efficient operation as well as its low cost (Tan et al., 2021). Unlike the metal-containing photocatalysts that need expensive metal salts for preparation, g-C₃N₄ is primarily produced by thermal polymerization of cheap N-rich precursors such as dicyandiamide, melamine, cyanamide, urea, and guanidine hydrochloride at various temperatures (Prasad et al., 2019; Reddy et al., 2019; Ye et al., 2015; Zhu et al., 2014). Urea was found to be a

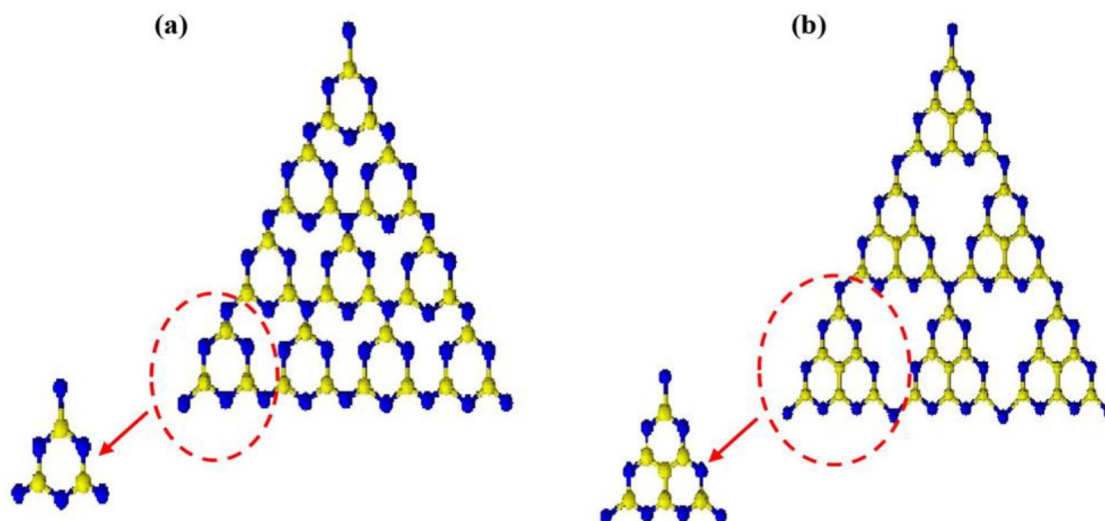


Figure 5. s-Triazine (a and b) tri-s-Triazine (heptazine) structures of g-C₃N₄ (Mousavi et al., 2018).

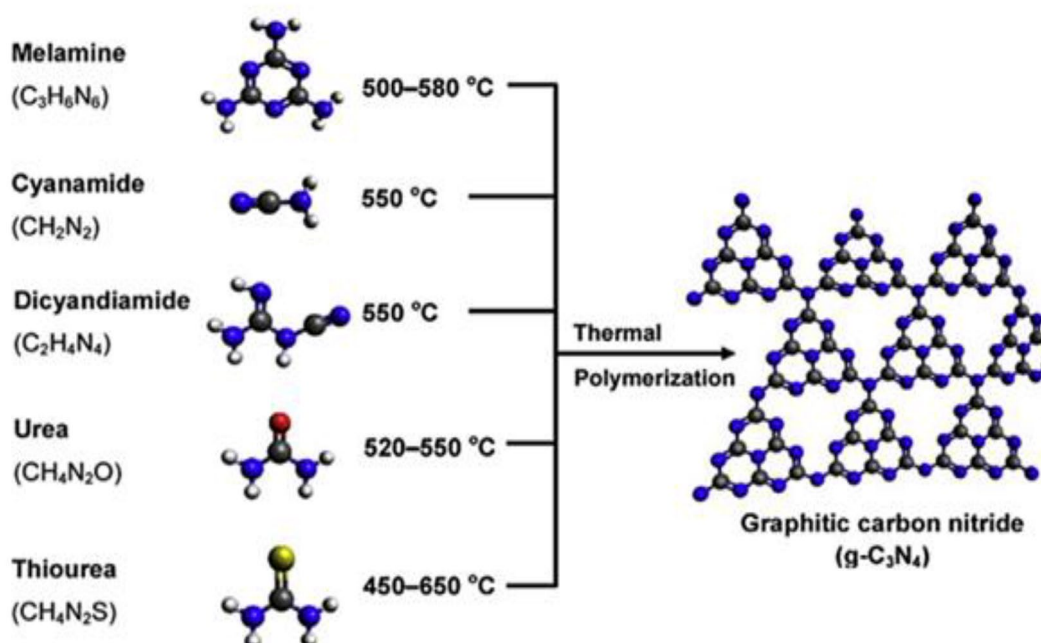


Figure 6. Synthesis of graphitic carbon nitride using different precursors (Tahir et al., 2020).

superior precursor for preparing thin-layer g-C₃N₄ with a high specific surface area among the numerous precursors utilized to synthesize g-C₃N₄ (Cao et al., 2015). The temperature at which g-C₃N₄ is synthesized is determined by the type of precursor used, whereas the thickness of the g-C₃N₄ layers is determined by the pyrolysis time (Figure 6) (Tahir et al., 2020).

Modification strategies of g-C₃N₄ photoactivity

Since its discovery in 2009, scientists have worked hard to improve the photocatalytic performance of g-C₃N₄ and address its shortcomings, such as high rate of electron-hole recombination, insufficient visible light absorption ($\lambda < 460$ nm), low specific surface area (~ 10 m²/g), small active sites for interfacial

photoreactions, slow surface reaction kinetics, moderate oxidation ability, grain boundary effects, low charge mobility, and low quantum yield are the main disadvantages of g-C₃N₄ as photocatalyst (Sudhaik et al., 2018; Tahir et al., 2020). To improve photocatalytic activity, some major strategies have been developed, including (i) doping with metallic/non-metallic elements, (ii) coupling with other semiconductors, (iii) fabrication of mesoporous structures, and so on (Sudhaik et al., 2018).

Elemental doping of g-C₃N₄. Doping of g-C₃N₄ is a process of introducing foreign impurities into the g-C₃N₄ framework to enhance the inherent optical, electronic, luminescent, and physical properties of g-C₃N₄. In the field of photocatalysis,

band gap engineering of g-C₃N₄ via doping plays a predominant role to modulate the light absorption and redox band potentials for targeted photocatalytic applications (Ong et al., 2016).

Elemental doping is an effective strategy not only modifies the electronic band structure of g-C₃N₄ but also affects the surface properties, and improves the photocatalytic efficiency of g-C₃N₄ (Liu et al., 2021; Patnaik et al., 2021). Metal doping and nonmetal doping are the two main types of elemental doping. Metal doping endows some excellent functions to g-C₃N₄, such as reducing band gap, enhancing visible light absorption, and enhancing catalytic performance. These metals include alkali metals (Li, Na, K) and transition metals (Fe, Cu, and W), and so on (Liu et al., 2021). Metallic impurities introduce additional binding functions, lowering the bandgap and increasing visible light absorption, giving the doped system distinct catalytic and photocatalytic capabilities. To introduce metal ions into graphitic carbon nitrides, the matching soluble salt is commonly combined with the graphitic carbon nitride precursor and dissolved in deionized water while stirring to ensure uniformity (Dong et al., 2014).

Non-metal doping has proven to be an effective method to control electronic systems and improve visible light absorption (Xiao et al., 2020). Besides, Non-metal doping is a viable technique to inject heteroatoms and defects into the g-C₃N₄ matrix while keeping the metal-free characteristic. Because non-metal atoms have higher ionization energy and a different electronegativity, they can react with other substances to obtain electrons for covalent bond formation after being introduced to change the electron distribution surrounding the doped position due to charge polarization. Generally, highly electronegative doped-heteroatoms encourage electron migration from adjacent C atoms to the doping site and empower C atoms with induced polarization to demolish chemical inertia and create new reactive sites. At the same time, Lower electronegative heteroatom doping increased the asymmetric spin density of neighboring C atoms and enhanced the electron giving capacity of g-C₃N₄. These characteristics make the introduction of adsorption and activation sites and accelerate electron transfer rate. Up to now, Nonmetal heteroatoms such as C, S, and O have been highlighted in the doping modification of g-C₃N₄ (Tan et al., 2021). Recently, various excellent review articles have been carried out on improving the photocatalytic performance of g-C₃N₄ using metal and nonmetal doping (Hasija et al., 2019; Jiang et al., 2017; Liu et al., 2021; Starukh & Praus, 2020; Zhou, Zhang, et al., 2016).

Coupling with other semiconductors. The fast recombination of photoinduced electron-hole pairs causes the low efficiency of photocatalytic reactions and limited their practical photocatalytic applications. To suppress the recombination rate of photogenerated charge carriers, combining g-C₃N₄ with other semiconductors to form heterojunctions can not only improve

the separation of photogenerated charge carriers but also broaden the solar light absorption spectrum (Ye et al., 2015). In general, the heterojunctions should have appropriate band positions of the two semiconductors for energy-level offsets, resulting in the accumulation of space charge at the interfaces of the two components to facilitate the separation of photogenerated carriers. Because of their excellent physical, optical, and electrical properties, g-C₃N₄-based heterojunction nanocomposites have been widely used to address a wide range of environmental pollution and energy shortages when irradiated to visible light (Huang et al., 2018). There have been comprehensive reviews on the preparation and applications of g-C₃N₄/TiO₂ heterojunctions to which readers can refer (Acharya & Parida, 2020; Zhou et al., 2017). Herein this review mainly focuses on different types of g-C₃N₄/TiO₂-based heterojunctions for photodegradation of organic pollutants, which are presented in Tables 1 to 3.

Fabrication of mesoporous structure. As a polymer, g-C₃N₄ has a flexible structure and is thus well suited to form different morphologies (Cao et al., 2015). Controlled morphologies and surface characteristics of the g-C₃N₄ nanostructure matrix are an effective technique to advance g-C₃N₄ photocatalysis with efficient charge transportation and migration as well as mass diffusion during the photocatalytic reaction (Ong et al., 2016). Indeed, several typical nanostructures of g-C₃N₄ have been obtained, such as porous g-C₃N₄, hollow spheres, and 1D nanostructures (Cao et al., 2015). Controlling the nanostructure may lead to modifications in the chemical, physical, and optical properties of g-C₃N₄. The number of redox sites, diffusion distance of electrons, and holes to reach these sites can be tuned by controlling the nanostructure (Mishra et al., 2019). Porous g-C₃N₄ photocatalysts are extremely fascinating, which can significantly increase their exposed surface area and accessible channels (porosity) and active sites in g-C₃N₄, thus facilitating the molecular mass transfer/transport, charge migration and separation, surface reactions, and light-harvesting (Cao et al., 2015; Wen et al., 2017). Moreover, g-C₃N₄ precursors like cyanamide, urea, dicyanamide, and melamine can be mixed with specific templates like silica materials, then thermally condensed. This produces a g-C₃N₄/template component, which is then removed with ammonium hydrogen fluoride or hydrofluoric acid to yield a porous g-C₃N₄ structure (Jourshabani et al., 2020; Thomas et al., 2008; Wang, Wang, & Antonietti, 2012). For instance, Shi et al. successfully synthesized spherical mesoporous g-C₃N₄ using cyanamide as a precursor and spherical mesoporous silica as a sacrificial template. The experimental results showed that as-prepared spherical g-C₃N₄ with a porous structure had a much larger surface area than bulk g-C₃N₄ for decomposing RhB under visible light, as well as excellent recycling activity (Shi et al., 2019). Similarly, Li, Huang, et al. (2018) prepared high-surface-area mesoporous

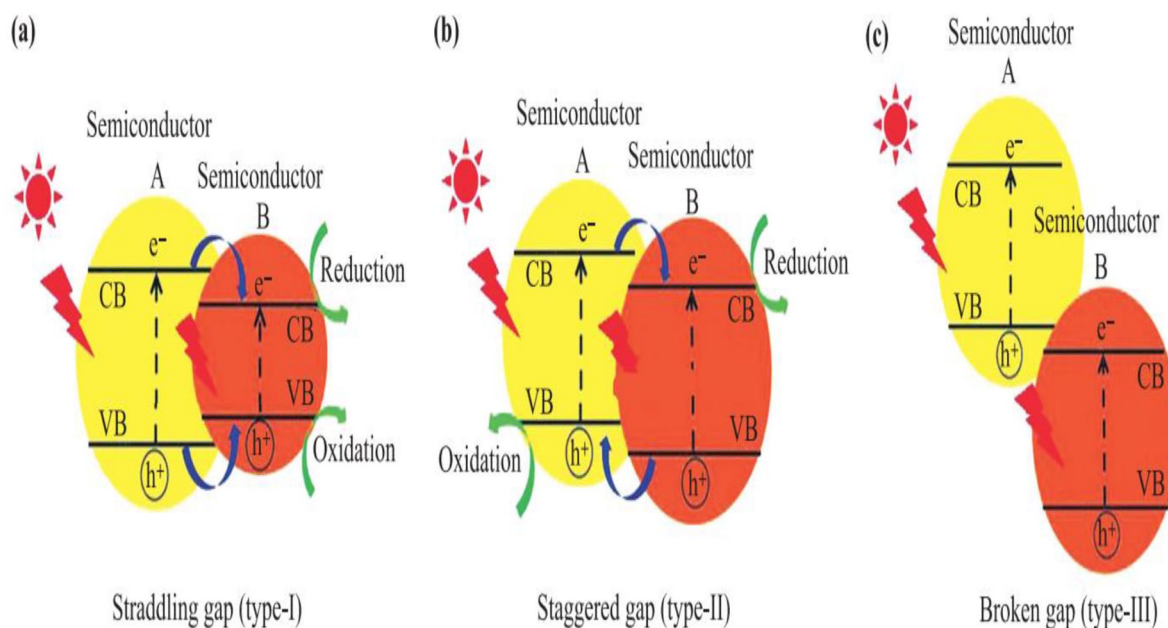


Figure 7. Schematic illustration of the mechanism of separation of electron-hole pairs in conventional heterojunction photocatalysts: (a) type-I, (b) type-II, and (c) type-III heterojunctions (Zhou et al., 2021).

g-C₃N₄ nanosheets with excellent adsorption capacity and photocatalytic activity by directly polycondensation urea followed by a one-step thermal exfoliation strategy.

Applications of g-C₃N₄/TiO₂ Heterojunction Nanocomposites for Photodegradation of Organic Pollutants

When g-C₃N₄ and TiO₂ are combined to form a g-C₃N₄/TiO₂ heterojunction, photocatalytic activity is significantly increased compared to single-component catalysts, making g-C₃N₄/TiO₂ a promising candidate for organic pollutant degradation in wastewater (Zhou et al., 2017). Due to their high activity, high thermal and chemical stability, and well-matched band structure, heterojunction catalysts made of g-C₃N₄ and TiO₂ have recently received a lot of attention. Various kinds of g-C₃N₄/TiO₂ heterojunction nanocomposite catalysts have been developed to solve water pollution problems. Meanwhile, in the case of wastewater treatment, g-C₃N₄/TiO₂ heterojunction nanocomposites have been widely used to degrade organic contaminants including rhodamine B (RhB), methyl orange (MO), methylene blue (MB), phenol, and so on. Summary of the recent progress on the photodegradation of organic pollutants using g-C₃N₄/TiO₂-based heterojunction nanocomposites are shown in Tables 1 to 3. Therefore, this review mainly focuses on type II, all-solid-state Z-scheme, and direct Z-scheme g-C₃N₄/TiO₂-based heterojunctions for photocatalytic decomposition of the organic contaminants from wastewater.

Conventional heterojunction photocatalytic systems

Heterojunction catalyst is one of the most popular terms in the catalytic field in recent years, and it is made up of two

different band structure semiconductor catalysts that contact each other to form a catalyst heterojunction structure (Zhou et al., 2017). Heterojunction catalysts exhibit strong optical absorption ability and higher carrier utilization efficiency than single-component semiconductor catalysts. Therefore, the built-in electrostatic field of heterojunction catalyst is an effective strategy to promote the separation and transfer of photo-induced charge carriers to maximize the utilization of absorbed photons and improve photocatalytic efficiency (Wang & Liu, 2019).

As shown in Figure 7, there are typically three types of conventional heterojunction photocatalysts; straddling gap (type-I), staggered gap (type-II), and broken gap (type-III) (Low, Yu, et al., 2017; Ong et al., 2016). For type I heterojunctions, the e⁻ and h⁺ pairs migrate to the CB and VB of the semiconductor B, respectively. The charge carriers in the type I heterojunction photocatalyst cannot effectively separate due to their accumulation in the same semiconductor (Zhou et al., 2021).

In type-II heterojunctions, the conduction band (CB) and valence band (VB) position of semiconductor A are higher than that of the conduction band (CB) and valence band (VB) position of semiconductor B as shown in Figure 7b. Thus, the photogenerated electrons will transfer to semiconductor B, while the photogenerated holes will migrate to semiconductor A under light irradiation, resulting in a spatial separation of electron-hole pairs. Type-III photocatalyst heterojunction is similar to the type-II photocatalyst heterojunction, except that the band gaps do not overlap. As a result, electron-hole migration and separation between the two semiconductors are impossible in the type-III heterojunction, making it unsuitable for improving electron-hole pair separation (Low, Yu, et al., 2017).

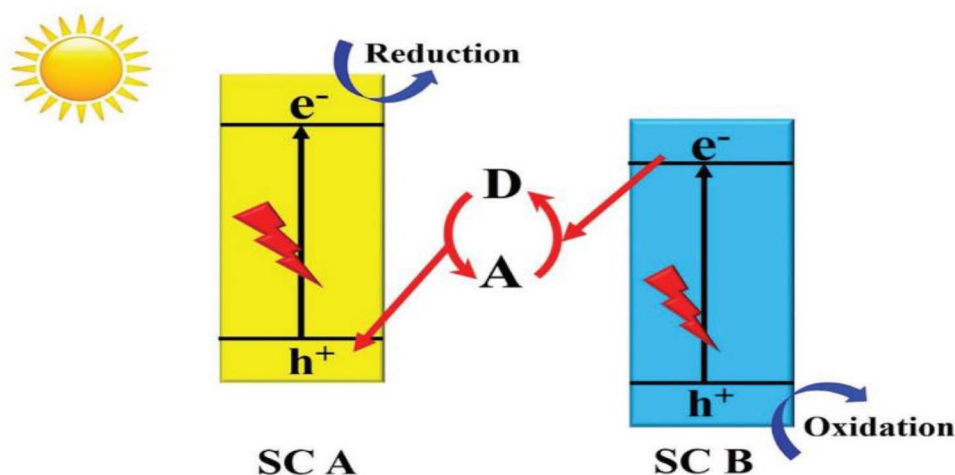


Figure 8. Schematic illustration of liquid-phase Z-scheme photocatalytic system, where A and D respectively represent the electron acceptor and donor (Low, Jiang, et al., 2017).

Because of the spatial separation of photogenerated e^- and h^+ pairs, type-II heterojunction is the most successful among other types of conventional heterojunctions (Kumar, Khan, et al., 2020). The poor redox ability of type-II heterojunction photocatalysts limits their use in a wide range of applications (Low, Jiang, et al., 2017). However, recent efforts have been made to construct an efficient $g\text{-C}_3\text{N}_4/\text{TiO}_2$ -based type-II heterojunction structure that may considerably boost the separation of photo-generated charge carriers, as well as the photocatalytic activity of the catalyst. Meanwhile, the photocatalytic performance of $g\text{-C}_3\text{N}_4/\text{TiO}_2$ heterojunction catalysts is good, making them suitable for the degradation of organic pollutants in wastewater (Zhou et al., 2017). In the development of type-II heterojunction, $g\text{-C}_3\text{N}_4/\text{TiO}_2$ composite is famous, where photo-excited electrons transferred to TiO_2 for oxidation and holes were transferred to $g\text{-C}_3\text{N}_4$ monolayer for a redox reaction, resulting in inhibited charge carrier recombination (Tahir et al., 2020).

Because of the excellent spatial separation of photogenerated electron-hole pairs, only type-II heterojunction is acceptable for constructing effective photocatalysts for the application of different organic pollutant degradation in wastewater, according to the aforementioned investigation (Zhou et al., 2021). Hence, a robust redox ability in type-II heterojunctions is difficult to achieve. In contrast to the traditional Type-II heterojunction, a novel type of heterojunction called a Z-scheme heterojunction has just been described to overcome this shortcoming (Ong et al., 2016).

All-solid-state indirect Z-scheme $g\text{-C}_3\text{N}_4\text{-TiO}_2$ heterojunction photocatalysts

In nature, It is well known that green plants can effectively convert CO_2 and H_2O to O_2 and carbohydrates through natural photosynthesis, whereby the photogenerated electrons are transported through a Z-scheme mode (Zhang et al., 2020). Furthermore, the photosynthesis of plants generally proceeds

according to the so-called Z-scheme photocatalytic process, in which two isolated reactions of water oxidation and CO_2 reduction are linked together through the redox mediators (Wen et al., 2017). Typically, in a traditional Z-scheme photocatalytic system two distinct photocatalysts are linked through a suitable shuttle redox ion mediator (viz. an electron acceptor/donor (A/D) pair). The commonly used shuttle redox ion pairs are $\text{Fe}^{3+}/\text{Fe}^{2+}$ and IO_3^-/I^- , which usually serve as electron transfer chains (Low, Jiang et al., 2017; Xu, Zhang et al., 2018).

As shown in Figure 8, both semiconductor A and semiconductor B are photoexcited when irradiated to light, resulting in the generation of electrons and holes in their respective CB and VB. The photogenerated electrons from semiconductor B will then move through a shuttle redox mediator to the VB of semiconductor A, leaving photogenerated holes in the VB of semiconductor B. As a result, the photogenerated electrons remain on semiconductor A with the greater reduction potential, while the photogenerated holes remain on semiconductor B with the higher oxidation potential, resulting in the optimization of the photocatalytic system's redox potential (Low, Jiang, et al., 2017).

However, Traditional Z-scheme photocatalysts have various limitations such as redox mediator-induced reverse reactions, in particular, is thermodynamically favorable and can readily occur because photogenerated electrons and holes with high redox power are consumed by shuttle redox ion pairs. Furthermore, the light-shielding effect, practicality constrained in solution systems, sluggish charge carrier transfer rate limited by ion-pair diffusion, and solution pH sensitivity can all contribute to traditional Z-scheme photocatalysts' limited applicability. Moreover, Most redox mediators are unstable and tend to deactivate, resulting in a reduction in reaction rate (Xu, Zhang, et al., 2018).

Tada et al. (2006) first proposed the concept of an all-solid-state Z-scheme photocatalyst, which consisted of two different semiconductors and a solid electron mediator between them.

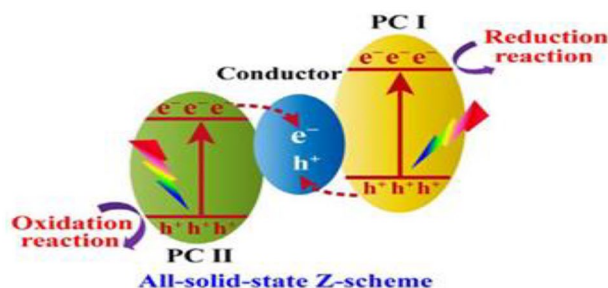


Figure 9. Schematic illustrations of charge carrier transfer mechanism in all-solid-state Z-scheme photocatalysts (Xu, Zhang, et al., 2018).

Meanwhile, For the all-solid-state Z-scheme photocatalytic system with the Ohmic-contact interfaces, their photocatalytic activities are majorly dependent on the surface properties of semiconductors with higher conduction band (CB) and valance band (VB) edges, thus leading to the robust redox ability and enhanced Photocatalytic activity. Each semiconductor in the Z-scheme photocatalytic system is responsible for one oxidation and the other for reduction reaction, thus helping for achieving the extremely extended visible-light absorption, strengthened redox ability, improved photostability, charge-separation, and photocatalytic efficiency (Wen et al., 2017).

Since the first report, Z-scheme Photocatalysis has become a promising solution for resisting environmental degradation and the global energy crisis. It works on the principle of effective separation of photogenerated electron-hole pairs and optimizes the oxidation and reduction ability of the photocatalytic system (Huang et al., 2019). Meanwhile, a Z-scheme photocatalyst may be designed based on the bandgap alignment idea to maximize photogenerated charge carrier lifetimes by suppressing charge carrier recombination for improved photocatalytic performance in the visible light spectrum (Younis & Kim, 2020).

In all-solid-state Z-scheme photocatalyst systems, the selection of a proper electron mediator is crucial because it can both efficiently transfer the photoinduced charge carriers and improve the stability of the photocatalysts. Mostly Noble metals, such as Au, Ag, and Cu NPs, have been used as excellent electron mediators for constructing all-solid-state Z-scheme photocatalysts. In addition, other carbon materials (eg, graphene, GO, RGO, CNTs) are also good candidates for electron mediators (Figure 9) (Xu, Zhang, et al., 2018).

Generally, the photocatalytic performance of Z-scheme photocatalysts is superior to that of the conventional type-II heterojunction and traditional Z-scheme photocatalytic system (Huang et al., 2019; Low, Jiang, et al., 2017). The narrower g-C₃N₄ energy bandgap (~2.7 eV) compared to TiO₂ (~3.2 eV) opens possibilities to use them in visible-light-driven photocatalysis. Furthermore, the high position of the conduction band (CB) of g-C₃N₄ enriches it with high photocatalytic reduction power and the high position of the valence band (VB) position of TiO₂ is responsible for high oxidation

power (Giannakopoulou et al., 2017). Therefore, the idea of coupling TiO₂ with g-C₃N₄ has been approved to be a promising approach to obtaining highly active photocatalysts with a visible light response and high charge carriers' separation efficiency due to their matched band structures and synergistic effects (Lu et al., 2018). Despite the attempts in structure design, conventional-type-II heterojunctions between g-C₃N₄ and TiO₂ suffer from decreasing the reduction capability of the electrons and oxidation capability of the holes after they migrate to the lower energy levels, owing to the photo-generated electrons and holes transferring to less negative and positive band sites. Therefore, to address this problem proper design of all-solid-state indirect Z-scheme photocatalytic heterojunction is significantly needed. Different from type-II heterojunction, the all-solid-state indirect Z-scheme charge transfer route could not only promote spatially charge separation, but also retain the strong redox ability of both TiO₂ and g-C₃N₄ (Liu, Zeng, et al., 2019; Lu et al., 2018).

In particular, it has been widely demonstrated that the formation of the all-solid-state Z-scheme g-C₃N₄-TiO₂ photocatalysts by different preparation methods has attracted intensive attention due to their superior photocatalytic performances. As a result, most TiO₂/g-C₃N₄ composites have been prepared by various synthesis methods including the hydrothermal method, sol-gel method, and have been widely used in many photocatalytic studies, including degradation of organic pollutants in wastewater, air purification, carbon dioxide reduction, and production of H₂ by water splitting, etc. (Lu et al., 2018).

In recent years, it has been reported that the combination of g-C₃N₄ and TiO₂ was a good candidate for the construction of the all-solid-state Z-scheme photocatalytic system. In an all-solid-state Z-scheme photocatalytic system, the photogenerated electrons prefer to remain in the conduction band (CB) of g-C₃N₄, and holes are stored in the valence band (VB) of TiO₂. Subsequently, the two oxidation and reduction processes take place simultaneously on the VB of TiO₂ and CB of g-C₃N₄, respectively. Remarkably, these two processes take place in separate places of the solid, greatly enhancing the photocatalytic efficiency (Xiao et al., 2019). This Z-scheme transfer mechanism greatly reduces the recombination rate of the electron-hole pair, thereby improving the photocatalytic activity (Bi et al., 2020). Due to the merits of the well-matched band structure of g-C₃N₄ and TiO₂, many groups have worked for years to construct effective all-solid-state Z-scheme g-C₃N₄/TiO₂ heterojunctions (Jiang et al., 2018).

In general, in the all-solid-state indirect Z-scheme g-C₃N₄-TiO₂ based photocatalysts, photo-generated electrons on TiO₂ recombine with holes on g-C₃N₄ through the electron mediators to accomplish effective separation of photo-generated electron-hole pairs with robust redox ability. Meanwhile, the particular active site and its active catalytic capability are critical to the catalytic process (Wang & Liu, 2019). In particular,

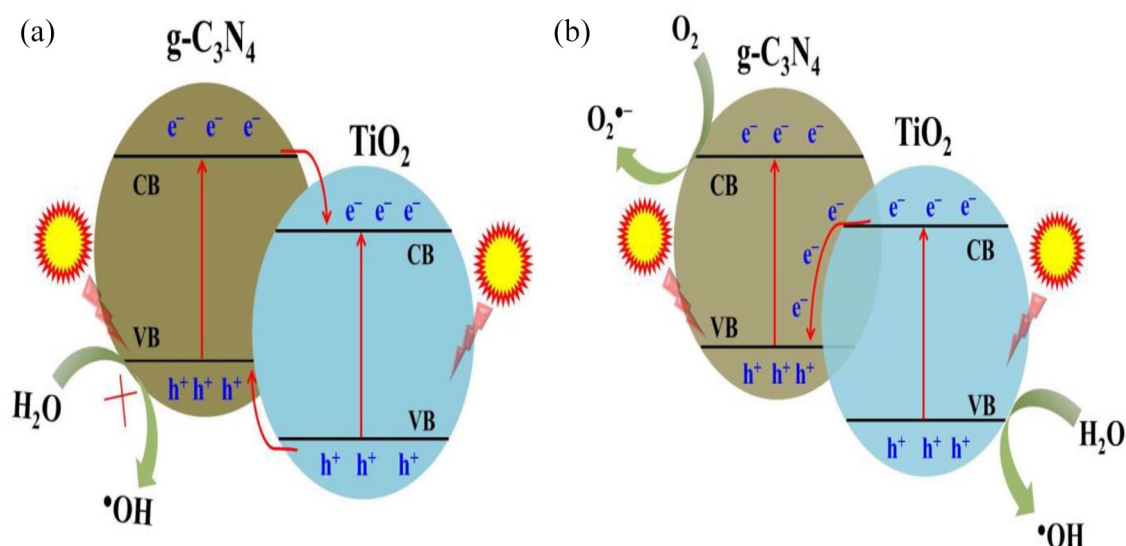


Figure 10. Schematic of electron-hole transfer mechanism of g-C₃N₄-TiO₂ type-II heterojunction (a and b) the direct Z-scheme g-C₃N₄-TiO₂ (Jo & Natarajan, 2015).

TiO₂ and g-C₃N₄ can form an all-solid-state Z-scheme heterojunction due to their matched conduction band (CB) and valence band (VB) positions, which can not only overcome the intrinsic defects of pristine photocatalyst but can also maintain the strong redox ability (Zhao et al., 2020). Moreover, coupling of narrow band-gap g-C₃N₄ with TiO₂ nanotube to construct an all-solid-state Z-scheme visible-light photocatalytic system could simultaneously possess the high charge-separation efficiency and robust redox ability under visible-light irradiation, which may produce enhanced visible-light photocatalytic activity and good stability (Zhou, Chen, et al., 2016).

Direct Z-scheme g-C₃N₄-TiO₂ heterojunction photocatalysts

A direct Z-scheme is one in which two semiconductors are joined together without the need for redox-mediators or electron mediators. The photoinduced electron-hole-pair separation method is based on the intercross-sectional electron transfer mechanism (Natarajan et al., 2018). Specifically, a typical Z-scheme system has an electron transfer process pathway that resembles the English letter “Z” hence the name Z scheme. Moreover, the band structure of a direct Z-scheme photocatalyst is similar to that of a type-II heterojunction photocatalyst (Figure 10a and b), but its charge-carrier migration mechanism is different (Huang et al., 2019). During the photocatalytic reaction, the photogenerated electrons in TiO₂ with lower reduction ability recombine with the photogenerated holes in g-C₃N₄ with a lower oxidation ability (Figure 10b) (Low, Jiang, et al., 2017). However, Due to its low potential, the hole in the valence band of g-C₃N₄ is insufficient to oxidize OH to [•]OH radicals (Huang et al., 2015). Therefore, the photogenerated electrons in g-C₃N₄ with high reduction ability and photogenerated holes in TiO₂ with a high oxidation ability

can be maintained. As a result, the redox ability of the direct Z-scheme photocatalyst is significantly greater than that of the type II heterojunction photocatalyst. In addition, it should be noted that charge-carrier migration for the direct Z-scheme photocatalyst is physically more feasible than that of type-II heterojunction photocatalysts (Low, Jiang, et al., 2017).

Therefore, a direct Z-scheme can be successfully constructed if there is a suitable band structure matching between semiconductors (Tahir et al., 2020). Compared with conventional liquid phase Z-scheme and all-solid-state Z scheme photocatalytic systems, a direct Z-scheme photocatalytic system with direct contact between two components can omit the process of carriers passing through the electron mediator, greatly lowering the possibility of recombination of bulk electrons and holes. Moreover, direct Z-scheme Photocatalytic systems can reduce the cost of building photocatalytic systems, and overcome the light-shielding effect caused by the noble metal electron mediator which makes them the best candidate for water splitting, pollutant degradation, and CO₂ conversion (Huang et al., 2019). In addition, high VB and low CB are easier to generate direct Z-scheme, which has been testified to be a prospective modification for enhancing photocatalytic performance (Low, Jiang et al., 2017; Ni et al., 2021; Qi et al., 2017).

Recently, due to the relatively high cost of the commonly used electron mediators (eg, Pt, Ag, and Au), a new generation of direct Z-scheme heterojunctions without the electron mediators has attracted a great deal of attention (Low, Yu, et al., 2017). Wang, Liu, et al. (2009) constructed the first mediator-free direct Z-scheme photocatalytic system. However, Yu et al. (2013), prepared the first direct Z-scheme g-C₃N₄/TiO₂ photocatalyst without an electron mediator via a simple calcination route using inexpensive P25 and urea as feedstock, and its enhanced photocatalytic activities due to efficient separation of photo-induced charge carriers were evaluated via photocatalytic

oxidation of formaldehyde (HCHO) in the air under UV light irradiation. As a result, the transmission distance is reduced and the photocatalytic efficiency is increased (Yu et al., 2013).

In this brief review, the coupling of suitable energy band structures of $g\text{-C}_3\text{N}_4$ and TiO_2 to construct a direct Z-scheme photocatalytic system for photocatalytic decomposition of various organic contaminants has been explored in depth. In general, the direct Z-scheme $g\text{-C}_3\text{N}_4\text{-TiO}_2$ charges transfer method follows the following principles: The photo-generated electrons on TiO_2 recombine with holes on $g\text{-C}_3\text{N}_4$ through the built-in electrostatic field to accomplish effective separation of photo-generated electrons with higher reducibility and photo-generated holes with higher oxidizing characteristics. In the meanwhile, the particular active site and its active catalytic capability are critical to the catalytic process (Wang & Liu, 2019). Therefore, Direct Z-scheme $g\text{-C}_3\text{N}_4\text{-TiO}_2$ photocatalysts have numerous advantages due to their simple binary composition, high photocatalytic activity, ease of design, and ease of production. However, they have several drawbacks, including difficult control of the intimate Z-scheme interfaces with large surface area, insufficient visible-light absorption, slow reactant adsorption kinetics, and slow surface redox kinetics. Fortunately, these issues can be addressed by using an efficient electron mediator with a large surface area of earth-abundant two-dimensional conductive graphene (GR) or reduced graphene oxide (RGO) (Wu et al., 2017). Recent advances in the development of direct Z-scheme $g\text{-C}_3\text{N}_4/\text{TiO}_2$ -based heterojunctions for photodegradation of organic pollutants are presented in Table 3.

Boosting the Photocatalytic Activity of $g\text{-C}_3\text{N}_4/\text{TiO}_2$ -Based Nanocomposite Photocatalysts

Coupling $g\text{-C}_3\text{N}_4/\text{TiO}_2$ nanocomposites with graphene-based materials

The synthesis and use of carbon materials for photocatalytic applications have become a hot issue in materials research. Graphene, a unique kind of carbon material, was long considered to be thermodynamically unstable until the first experimental isolation of single-layer graphene in 2004. It has since been proved to be thermodynamically stable (Cheng et al., 2015).

Graphene has been a suitable 2D material for photocatalytic applications because of its unique properties such as ultrahigh theoretical specific surface area ($2,630\text{ m}^2\text{ g}^{-1}$), high chemical stability, excellent optical transmittance (97.7%), exceptional thermal conductivity ($5,000\text{ W m}^{-1}\text{ K}^{-1}$), superior mechanical properties with Young's modulus of 1,100 GPa and high electron mobility at room temperature ($200,000\text{ cm}^2\text{ V}^{-1}\text{ s}^{-1}$) (Chowdhury & Balasubramanian, 2014; Huang et al., 2016; Zhao et al., 2017). Meanwhile, Graphene is an excellent electron acceptor during the photocatalytic process due to its high electron mobility and extended $\pi\text{-}\pi$ conjugation structure, which can

inhibit the recombination of photoexcited electrons and holes. Therefore, graphene is applied in photocatalysis due to its high adsorption of organic pollutants, enhanced visible light absorption, and improved separation-transportation efficiency of photogenerated charge carriers (Meng & Zhang, 2018; Zhang et al., 2017). As result, the use of graphene in the field of heterogeneous Photocatalysis provides a new dimension to enhance photocatalytic performance (Chowdhury & Balasubramanian, 2014). Graphene has a multifaceted part in enhancing the photocatalytic properties of conventional semiconductors by acting as an adsorbent, photosensitizer, photo-stabilizer, and conductor as well as co-catalyst (Sabir et al., 2021). Because of these appealing properties, combining graphene with $g\text{-C}_3\text{N}_4$ and TiO_2 appears to be a promising method to improve photocatalytic performance (Gusain et al., 2019; Yahya et al., 2018). Graphene can significantly improve the photoactivity of C_3N_4 by effectively separating photo-induced electron-hole pairs and significantly improving charge transfer due to the formation of a well-defined electron-hole puddle at the graphene/ $g\text{-C}_3\text{N}_4$ interface (Huang et al., 2016).

For the synthesis of graphene-semiconductor-based nanocomposite photocatalysts, graphene oxide (GO) is often used as the precursor of graphene (Peiris et al., 2021). Moreover, a comprehensive review on the synthesis of graphene-based semiconductor material for photodegradation of organic pollutants is presented by Voon et al. (2016). Meanwhile, Putri et al. (2016) summarized the recent advances in the application of graphene oxide toward visible-light-driven photocatalysis. Graphene or reduced graphene oxide (rGO) can not only increase the specific surface area of the as-prepared composite but also improve its surface adsorption and reaction kinetics, resulting in a considerable increase in photocatalytic activity. The excellent electron transport capacity of reduced graphene oxide (rGO) was exploited to achieve the efficient separation of $g\text{-C}_3\text{N}_4$ photo-generated carriers (Hu et al., 2021; Prasad et al., 2019).

Similarly, reduced graphene oxide (rGO) is frequently used in the fabrication of heterojunction photocatalysts to increase the specific surface area and lower the recombination rate of photogenerated electron-hole pairs; as a result, photocatalytic performance is considerably improved (Hu et al., 2019). Therefore, many researchers have reported that the combination of TiO_2 and graphene-based materials (TiO_2/rGO) has intriguing photocatalytic properties such as high organic dye adsorption, suppressing photogenerated charge carrier recombination, and strong dye chromophores stacking which improves the photocatalytic activity (Huang et al., 2016). For instance, Fan et al. synthesized UV light-driven TiO_2/rGO binary nanocomposites through the sol-anaerobic calcination method for the degradation of phenol. The enhanced photocatalytic performance can be ascribed to the existence of rGO which can effectively promote the separation and transportation of photogenerated electron-hole pairs and inhibit the

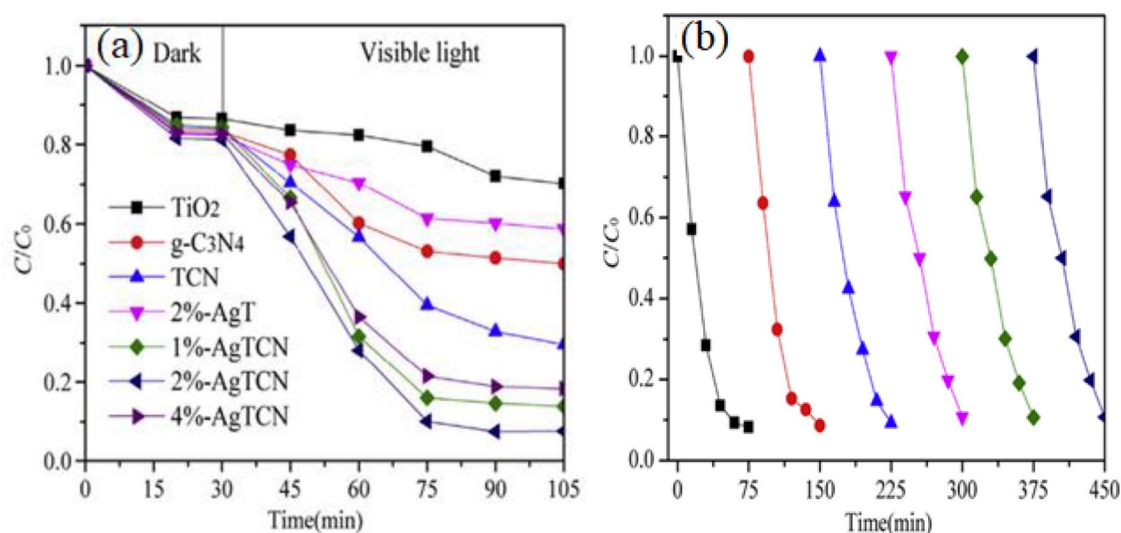


Figure 11. (a) Photocatalytic degradation of RhB under visible light irradiation and (b) recycling of the 2%-AgTCN for the removal of RhB dyes.

recombination rate of photoinduced electron-hole pairs. Moreover, TiO_2/rGO nanocomposite has a higher specific surface area and photocatalytic degradation efficiency of phenol than Pure TiO_2 (Fan et al., 2021). Subsequently, Wu et al. reported that introducing reduced graphene oxide (rGO) as an interfacial mediator into direct Z-scheme $\text{g-C}_3\text{N}_4\text{-TiO}_2$ nanocomposites can significantly improve photocatalytic activity. Meanwhile, rGO can not only act as an electron mediator to improve Z-scheme charge transportation and separation, but it can also increase the adsorption capacity of ternary composites toward the photodegradation of MB molecules. Moreover, rGO as an effective interfacial electron mediator may convert direct Z-scheme $\text{g-C}_3\text{N}_4\text{-TiO}_2$ photocatalysts to indirect Z-scheme photocatalysts with considerably improved photocatalytic efficiency, thus opening up new routes for fabricating earth-abundant ternary nanocomposite photocatalysts. Generally, diverse experimental investigations showed that rGO has multi-functional roles such as solid-state electron mediators, adsorbents, photosensitizers, and electron acceptors (Wu et al., 2017).

Constructing $\text{g-C}_3\text{N}_4/\text{TiO}_2$ -based ternary nanocomposites by deposition of plasmonic metal nanoparticles

Nanoparticles of noble metals (Ag, Au, Pd, and Pt) can strongly absorb visible light due to their localized surface plasmon resonance (LSPR), which can be tuned by varying their size, shape, and surrounding. Furthermore, noble metal NPs can also work as electron traps and active reaction sites. These factors gave rise to a new approach to efficient visible-light photocatalysts, namely, depositing the noble metal nanoparticles on the surface of a suitable semiconductor to form a metal-semiconductor composite photocatalyst (Dhiman, 2020; Wang et al., 2012). Moreover, the strong LSPR properties of Ag and Au make them the most attractive among the other metals (Prakash et al., 2018).

For example, Chai et al. fabricated $\text{g-C}_3\text{N}_4\text{-Pt-TiO}_2$ nanocomposites via facile chemical adsorption followed by a calcination method. Meanwhile, the Pt deposited on TiO_2 surfaces in the $\text{g-C}_3\text{N}_4\text{-TiO}_2$ nanocomposite can promote the separation of photogenerated electron-hole pairs, which can effectively inhibit the recombination of photogenerated charge carriers and improve the photocatalytic activity (Chai et al., 2012). Meanwhile, Chen et al. constructed a ternary composite of $\text{g-C}_3\text{N}_4/\text{Ag/TiO}_2$ microspheres for degradation of methyl orange under visible-light irradiation. In addition, the surface plasmon resonance effect of the Ag nanoparticles exhibited enhanced visible-light absorption and photocatalytic activity of $\text{g-C}_3\text{N}_4/\text{Ag/TiO}_2$ composites than the pure TiO_2 or $\text{g-C}_3\text{N}_4$. Moreover, the $\text{g-C}_3\text{N}_4/\text{Ag/TiO}_2$ microsphere sample showed better recyclability under visible-light irradiation (Chen et al., 2014). A similar effect was also observed by Sui et al. who prepared a $\text{g-C}_3\text{N}_4/\text{Ag/TiO}_2$ (AgTCN) ternary nanocomposite catalyst by varying the loading amount of Ag nanoparticles via a simple impregnation method. The photodegradation efficiency of Rhodamine B (RhB) over 2%-AgTCN composite catalyst was 3.1 times as high as that of TiO_2 and 2.15 times $\text{g-C}_3\text{N}_4$ within 105 minutes of reaction time (as shown Figure 11). Because a Schottky barrier is formed at the interface between the Ag and TiO_2 nanoparticles, the Ag nanoparticles can serve as electron conduction bridges, which accelerates the electronic transition between the close interfaces of Ag/TiO_2 and $\text{g-C}_3\text{N}_4$. As a result, the electrons generated by $\text{g-C}_3\text{N}_4$ migrate to the Ag/TiO_2 surface. This process makes it easy to separate light-induced electrons and holes in space that inhibit electron-hole recombination, and boosts photocatalytic activity. In addition, the surface plasmon resonance effect of the Ag nanoparticles can promote the absorption performance of visible light. Moreover, the 2%-AgTCN composite catalyst exhibited stable photocatalytic performance with a very low activity loss after going through six cycles, which shows that it is a promising material for the degradation of organic pollutants in wastewater (Sui et al., 2020).

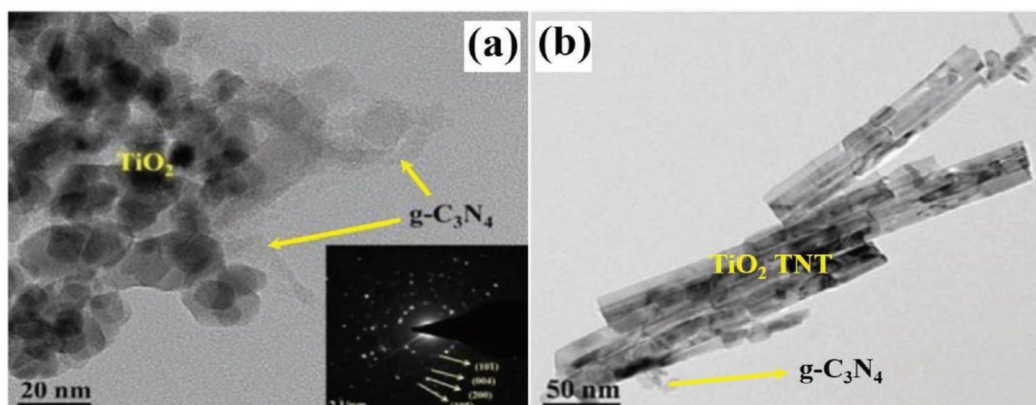


Figure 12. (a) TEM images of TiO_2 NPs/ $\text{g-C}_3\text{N}_4$ and (b) TiO_2 nanotubes (TiO_2 NTs)/ $\text{g-C}_3\text{N}_4$.

Ghafoor et al. synthesized $\text{g-C}_3\text{N}_4$ NS/ Ag/ TiO_2 NFS Z-scheme photocatalyst nanocomposites for environmental remediation for degradation of MB under simulated solar light irradiation. Moreover, the formation of Z-scheme heterojunction between TiO_2 and $\text{g-C}_3\text{N}_4$ and the surface plasmon resonance (SPR) effect of Ag nanoparticles are responsible for enhanced visible-light absorption, photocatalytic activity, and charge separation of these nanofiber composites (Ghafoor et al., 2019). Moreover, Zhang et al. synthesized Ag- TiO_2 /rGO nanocomposite via a solvothermal method for the removal of RhB dyes. Both the adsorbent and photocatalytic activity of all the Ag- TiO_2 /r-GO nanocomposites were much higher than pure TiO_2 . Therefore, the large BET surface area is responsible for the superior adsorbent capacity, while the suitable structure and photocatalytic properties of graphene and the localized surface plasmon (LSPR) effect of Ag nanoparticles are responsible for the improved photocatalytic activity (Zhang et al., 2017).

Morphology controlling

It is well known that TiO_2 morphology has a significant influence on its photocatalytic efficiency. Consequently, researchers have made great efforts to design a $\text{g-C}_3\text{N}_4$ / TiO_2 hybrid system with different TiO_2 morphologies such as nanoparticles, nanofibers, nanotubes, nanosheets, microspheres, and hollow nano box (Bi et al., 2020; Gündoğmuş et al., 2020; Ji et al., 2020; Jiang et al., 2017; Li, Sun, et al., 2018; Mishra et al., 2019; Sutar et al., 2020; Thomas et al., 2008; Zhou, Zhang, et al., 2016). For instance, Jo and Natarajan prepared two kinds of direct Z-scheme $\text{g-C}_3\text{N}_4$ / TiO_2 (NPs and NTs) heterojunctions via a facile wetness impregnation method for the degradation of isoniazid. The photoactivity of TiO_2 NTs/ $\text{g-C}_3\text{N}_4$ was higher than that of TiO_2 NPs/ $\text{g-C}_3\text{N}_4$ because the TiO_2 NTs/ $\text{g-C}_3\text{N}_4$ has a larger specific surface area than TiO_2 NPs/ $\text{g-C}_3\text{N}_4$ to provide a greater number of surface-active sites for photocatalytic reaction. Therefore, the heterojunction built from TiO_2 NTs and $\text{g-C}_3\text{N}_4$ NSs exhibited higher photoreactivity because the high surface area and tubular structure of TiO_2 NTs could

enhance the adsorption of pollutants and prolong the lifetime of the photogenerated charge carriers. Moreover, from this work, we can conclude that the rational tuning of the morphology of individual semiconductors is important for enhancing its photocatalytic activity (Figure 12) (Jo & Natarajan, 2015).

Conclusion and Perspectives

This review mainly focused on a comprehensive overview of the fundamental mechanisms of separation, and transportation of the photogenerated e^-/h^+ pairs of different types of $\text{g-C}_3\text{N}_4$ / TiO_2 based heterostructured nanocomposite photocatalysts for environmental decontamination of organic pollutants in wastewater. Depending on the charge-carrier separation mechanism, heterojunctions can be commonly grouped into type-II, all-solid-state Z-scheme, and direct Z-scheme photocatalytic heterojunctions. Among different types of heterojunctions formed using $\text{g-C}_3\text{N}_4$ and TiO_2 , the redox ability of charge carriers in type-II heterojunctions decreases due to the migration of photoinduced electrons and holes to lower conduction band and valance band energy levels respectively. However, the charge transfer mechanism may improve charge carrier separation and generate photoinduced electron-hole pairs with high redox abilities and increased photocatalytic activity for both all-solid-state and direct Z-scheme photocatalysts. Moreover, $\text{g-C}_3\text{N}_4$ / TiO_2 heterostructured photocatalytic materials have fascinating physicochemical properties that make them potentially useful for the applications of wastewater treatment. Meanwhile, with innovative design and thorough research of their superior photocatalytic activity, the applications of $\text{g-C}_3\text{N}_4$ / TiO_2 -based photocatalysts for the transformation of solar to chemical energy may be significantly increased more rationally. Furthermore, the fabrication of high-performance photocatalytic systems is required to create innovative, practical, and cost-effective photocatalysts with high activity, stability, efficiency, scalability, and selectivity. Despite substantial progress in the fabrication of efficient $\text{g-C}_3\text{N}_4$ / TiO_2 -based heterostructured photocatalysts, photocatalytic activity remains too low for practical applications. Therefore, both experimental testing methods and theoretical material simulation using first-principles

density functional theory (DFT) might be needed to further understand the photocatalytic properties and interfacial charge separation and transfer mechanism of g-C₃N₄/TiO₂ heterostructured photocatalysts. However, researchers have tried recent and practical endeavors to offer a clean environment by designing powerful photocatalytic materials using innovative synthesis techniques. Finally, Future advanced research efforts are needed to solve these issues in the near future.

Author contribution

AS: Writing – original draft, Conceptualization, Methodology, Data curation. MA: Supervision, Writing – review & editing. PA: Supervision, Writing – original draft, Writing – review & editing. EA: Supervision, Writing – review & editing.

Data Availability Statements

The datasets generated during and/or analyzed during the current study are available from the corresponding author on reasonable request.

Declaration of Conflicting Interests


The author(s) declared no potential conflicts of interest with respect to the research, authorship, and/or publication of this article.

Funding

The author(s) received no financial support for the research, authorship, and/or publication of this article.

ORCID iDs

Agidew Sewnet  <https://orcid.org/0000-0002-2430-2690>

Perumal Asaithambi  <https://orcid.org/0000-0002-0533-0178>

REFERENCES

- Acharya, R., & Parida, K. (2020). A review on TiO₂/g-C₃N₄ visible-light- responsive photocatalysts for sustainable energy generation and environmental remediation. *Journal of Environmental Chemical Engineering*, 8, 103896. <https://doi.org/10.1016/j.jece.2020.103896>
- Ahmed, S. N., & Haider, W. (2018). Heterogeneous photocatalysis and its potential applications in water and wastewater treatment: A review. *Nanotechnology*, 29, 342001. <https://doi.org/10.1088/1361-6528/aac6ea>
- Augugliaro, V., Palmisano, G., Palmisano, L., & Soria, J. (2019). Heterogeneous photocatalysis and catalysis: An overview of their distinctive features. In G. Marci & L. Palmisano (Eds.), *Heterogeneous photocatalysis: Relationships with heterogeneous catalysis and perspectives* (pp. 1–24). Elsevier. <https://doi.org/10.1016/B978-0-444-64015-4.00001-8>
- Babuponnusami, A., & Muthukumar, K. (2014). A review on Fenton and improvements to the Fenton process for wastewater treatment. *Journal of Environmental Chemical Engineering*, 2, 557–572. <https://doi.org/10.1016/j.jece.2013.10.011>
- Basavarajappa, P. S., Patil, S. B., Ganganagappa, N., Reddy, K. R., Raghu, A. V., & Reddy, C. V. (2020). Recent progress in metal-doped TiO₂, non-metal doped/codoped TiO₂ and TiO₂ nanostructured hybrids for enhanced photocatalysis. *International Journal of Hydrogen Energy*, 45, 7764–7778. <https://doi.org/10.1016/j.ijhydene.2019.07.241>
- Bi, X., Yu, S., Liu, E., Liu, L., Zhang, K., Zang, J., & Zhao, Y. (2020). Construction of g-C₃N₄/TiO₂ nanotube arrays Z-scheme heterojunction to improve visible light catalytic activity. *Colloids and Surfaces A Physicochemical and Engineering Aspects*, 603, 125193. <https://doi.org/10.1016/j.colsurfa.2020.125193>
- Burdett, J. K., Hughbanks, T., Miller, G. J., Richardson, J. W., & Smith, J. V. (1987). Structural-electronic relationships in inorganic solids: Powder neutron diffraction studies of the rutile and anatase polymorphs of titanium dioxide at 15 and 295 K. *Journal of the American Chemical Society*, 109, 3639–3646. <https://doi.org/10.1021/ja00246a021>
- Bustillo-Lecompte, C. (Ed.). (2015). *Advanced oxidation processes—Applications, trends, and prospects*. IntechOpen.
- Byrne, C., Subramanian, G., & Pillai, S. C. (2018). Recent advances in photocatalysis for environmental applications. *Journal of Environmental Chemical Engineering*, 6, 3531–3555. <https://doi.org/10.1016/j.jece.2017.07.080>
- Cao, S., Low, J., Yu, J., & Jaroniec, M. (2015). Polymeric photocatalysts based on graphitic carbon nitride. *Advanced Materials*, 27, 2150–2176. <https://doi.org/10.1002/adma.201500033>
- Chai, B., Peng, T., Mao, J., Li, K., & Zan, L. (2012). Graphitic carbon nitride (g-C₃N₄)–Pt–TiO₂ nanocomposite as an efficient photocatalyst for hydrogen production under visible light irradiation. *Physical Chemistry Chemical Physics*, 14, 16745–16752. <https://doi.org/10.1039/c2cp42484c>
- Cheng, N., Tian, J., Liu, Q., Ge, C., Qusti, A. H., Asiri, A. M., Al-Youbi, A. O., & Sun, X. (2013). Au-nanoparticle-loaded graphitic carbon nitride nanosheets: Green photocatalytic synthesis and application toward the degradation of organic pollutants. *ACS Applied Materials & Interfaces*, 5, 6815–6819. <https://doi.org/10.1021/am401802r>
- Cheng, Y., Fan, Y., Pei, Y., & Qiao, M. (2015). Graphene-supported metal/metal oxide nanohybrids: Synthesis and applications in heterogeneous catalysis. *Catalysis Science & Technology*, 5, 3903–3916. <https://doi.org/10.1039/c5cy00630a>
- Chen, X., & Mao, S. S. (2007). Titanium dioxide nanomaterials: Synthesis, properties, modifications and applications. *ChemInform*, 38, 2891–2959. <https://doi.org/10.1002/chin.200741216>
- Chen, Y., Huang, W., He, D., Situ, Y., & Huang, H. (2014). Construction of heterostructured g-C₃N₄/Ag/TiO₂ microspheres with enhanced photocatalysis performance under visible-light irradiation. *ACS Applied Materials & Interfaces*, 6, 14405–14414. <https://doi.org/10.1021/am503674e>
- Chen, Z., Zhang, S., Liu, Y., Alharbi, N. S., Rabah, S. O., Wang, S., & Wang, X. (2020). Synthesis and fabrication of g-C₃N₄-based materials and their application in elimination of pollutants. *The Science of the Total Environment*, 731, 139054. <https://doi.org/10.1016/j.scitotenv.2020.139054>
- Chowdhury, S., & Balasubramanian, R. (2014). Graphene/semiconductor nanocomposites (GSNs) for heterogeneous photocatalytic decolorization of wastewaters contaminated with synthetic dyes: A review. *Applied Catalysis B: Environmental*, 160–161, 307–324. <https://doi.org/10.1016/j.apcatb.2014.05.035>
- Daghrir, R., Drogui, P., & Robert, D. (2013). Modified TiO₂ for environmental photocatalytic applications: A review. *Industrial & Engineering Chemistry Research*, 52, 3581–3599. <https://doi.org/10.1021/ie303468t>
- Darkwah, W. K., & Oswald, K. A. (2019). Photocatalytic applications of heterostructure graphitic carbon nitride: Pollutant degradation, hydrogen gas production (water splitting), and CO₂ reduction. *Nanoscale Research Letters*, 14, 234. <https://doi.org/10.1186/s11671-019-3070-3>
- Dewil, R., Mantzavinos, D., Poullos, I., & Rodrigo, M. A. (2017). New perspectives for advanced oxidation processes. *Journal of Environmental Management*, 195, 93–99. <https://doi.org/10.1016/j.jenvman.2017.04.010>
- Dhiman, M. (2020). Plasmonic nanocatalysis for solar energy harvesting and sustainable chemistry. *Journal of Materials Chemistry A*, 8, 10074–10095. <https://doi.org/10.1039/d0ta03114c>
- Di Paola, A., Bellardita, M., & Palmisano, L. (2013). Brookite, the least known TiO₂ photocatalyst. *Catalysts*, 3, 36–73. <https://doi.org/10.3390/catal3010036>
- Dong, G., Zhang, Y., Pan, Q., & Qiu, J. (2014). A fantastic graphitic carbon nitride (g-C₃N₄) material: Electronic structure, photocatalytic and photoelectronic properties. *Journal of Photochemistry and Photobiology C Photochemistry Reviews*, 20, 33–50. <https://doi.org/10.1016/j.jphotochemrev.2014.04.002>
- Dong, P., Hou, G., Xi, X., Shao, R., & Dong, F. (2017). WO₃-based photocatalysts: Morphology control, activity enhancement and multifunctional applications. *Environmental Science Nano*, 4, 539–557. <https://doi.org/10.1039/c6en00478d>
- Dong, S., Feng, J., Fan, M., Pi, Y., Hu, L., Han, X., Liu, M., Sun, J., & Sun, J. (2015). Recent developments in heterogeneous photocatalytic water treatment using visible light-responsive photocatalysts: A review. *RSC Advances*, 5, 14610–14630.
- Etacheri, V., Di Valentin, C., Schneider, J., Bahnemann, D., & Pillai, S. C. (2015). Visible-light activation of TiO₂ photocatalysts: Advances in theory and experiments. *Journal of Photochemistry and Photobiology C Photochemistry Reviews*, 25, 1–29. <https://doi.org/10.1016/j.jphotochemrev.2015.08.003>
- Fan, H., Yi, G., Zhang, Z., Zhang, X., Li, P., Zhang, C., Chen, L., Zhang, Y., & Sun, Q. (2021). Binary TiO₂/RGO photocatalyst for enhanced degradation of phenol and its application in underground coal gasification wastewater treatment. *Optical Materials*, 120, 111482. <https://doi.org/10.1016/j.optmat.2021.111482>
- Fu, J., Yu, J., Jiang, C., & Cheng, B. (2018). g-C₃N₄-based heterostructured photocatalysts. *Advanced Energy Materials*, 8, 1–31. <https://doi.org/10.1002/aenm.201701503>
- Fu, Y., Yin, Z., Qin, L., Huang, D., Yi, H., Liu, X., Liu, S., Zhang, M., Li, B., Li, L., Wang, W., Zhou, X., Li, Y., Zeng, G., & Lai, C. (2022). Recent progress of noble metals with tailored features in catalytic oxidation for organic pollutants degradation. *Journal of Hazardous Materials*, 422, 126950. <https://doi.org/10.1016/j.jhazmat.2021.126950>

- Ghafoor, S., Inayat, A., Aftab, F., Duran, H., Kirchhoff, K., Waseem, S., & Arshad, S. N. (2019). TiO₂ nanofibers embedded with g-C₃N₄ nanosheets and decorated with Ag nanoparticles as Z-scheme photocatalysts for environmental remediation. *Journal of Environmental Chemical Engineering*, 7, 103452. <https://doi.org/10.1016/j.jece.2019.103452>
- Giannakopoulou, T., Papailias, I., Todorova, N., Boukos, N., Liu, Y., Yu, J., & Trapalis, C. (2017). Tailoring the energy band gap and edges' potentials of g-C₃N₄/rTiO₂ composite photocatalysts for NO_x removal. *Chemical Engineering Journal*, 310, 571–580. <https://doi.org/10.1016/j.cej.2015.12.102>
- Gopalan, A. I., Lee, J. C., Saianand, G., Lee, K. P., Sonar, P., Dharmarajan, R., Hou, Y. L., Ann, K. Y., Kannan, V., & Kim, W. J. (2020). Recent progress in the abatement of hazardous pollutants using photocatalytic TiO₂-based building materials. *Nanomaterials*, 10, 1854. <https://doi.org/10.3390/nano10091854>
- Gündoğmuş, P., Park, J., & Öztürk, A. (2020). Preparation and photocatalytic activity of g-C₃N₄/TiO₂ heterojunctions under solar light illumination. *Ceramics International*, 46, 21431–21438. <https://doi.org/10.1016/j.ceramint.2020.05.241>
- Guo, Y., Xiao, L., Zhang, M., Li, Q., & Yang, J. (2018). An oxygen-vacancy-rich Z-scheme g-C₃N₄/Pd/TiO₂ heterostructure for enhanced visible light photocatalytic performance. *Applications of Surface Science*, 440, 432–439. <https://doi.org/10.1016/j.apsusc.2018.01.144>
- Gupta, S. M., & Tripathi, M. (2011). A review of TiO₂ nanoparticles. *Chinese Science Bulletin*, 56, 1639–1657. <https://doi.org/10.1007/s11434-011-4476-1>
- Gusain, R., Gupta, K., Joshi, P., & Khatri, O. P. (2019). Adsorptive removal and photocatalytic degradation of organic pollutants using metal oxides and their composites: A comprehensive review. *Advances in Colloid and Interface Science*, 272, 102009. <https://doi.org/10.1016/j.cis.2019.102009>
- Gusain, R., Kumar, N., & Ray, S. S. (2020). Factors influencing the photocatalytic activity of photocatalysts in wastewater treatment. In: E. Fosso-Kankeu, S. Pandey, & S. S. Ray (Eds.), *Photocatalysts in advanced oxidation processes for wastewater treatment* (pp. 229–270). Wiley Online Library. <https://doi.org/10.1002/9781119631422.ch8>
- Han, C., Wang, Y., Lei, Y., Wang, B., Wu, N., Shi, Q., & Li, Q. (2015). In situ synthesis of graphitic-C₃N₄ nanosheet hybridized N-doped TiO₂ nanofibers for efficient photocatalytic H₂ production and degradation. *Nano Research*, 8, 1199–1209. <https://doi.org/10.1007/s12274-014-0600-2>
- Hao, R., Wang, G., Jiang, C., Tang, H., & Xu, Q. (2017). In situ hydrothermal synthesis of g-C₃N₄/rTiO₂ heterojunction photocatalysts with high specific surface area for Rhodamine B degradation. *Applications of Surface Science*, 411, 400–410. <https://doi.org/10.1016/j.apsusc.2017.03.197>
- Hasija, V., Raizada, P., Sudhaik, A., Sharma, K., Kumar, A., Singh, P., Jonnalagadda, S. B., & Thakur, V. K. (2019). Recent advances in noble metal free doped graphitic carbon nitride based nanohybrids for photocatalysis of organic contaminants in water: A review. *Applied Materials Today*, 15, 494–524. <https://doi.org/10.1016/j.apmt.2019.04.003>
- Huang, D., Chen, S., Zeng, G., Gong, X., Zhou, C., Cheng, M., Xue, W., Yan, X., & Li, J. (2019). Artificial Z-scheme photocatalytic system: What have been done and where to go? *Coordination Chemistry Reviews*, 385, 44–80. <https://doi.org/10.1016/j.ccr.2018.12.013>
- Huang, D., Yan, X., Yan, M., Zeng, G., Zhou, C., Wan, J., Cheng, M., & Xue, W. (2018). Graphitic carbon nitride-based heterojunction photoactive nanocomposites: Applications and mechanism insight. *ACS Applied Materials & Interfaces*, 10, 21035–21055. <https://doi.org/10.1021/acsami.8b03620>
- Huang, M., Yu, J., Hu, Q., Su, W., Fan, M., Li, B., & Dong, L. (2016). Preparation and enhanced photocatalytic activity of carbon nitride / titania (001 vs 101 facets)/ reduced graphene oxide (g-C₃N₄ / TiO₂ / rGO) hybrids under visible light. *Appl. Surf. Sci.*, 389, 1084–1093. <https://doi.org/10.1016/j.apsusc.2016.07.180>
- Huang, Z., Sun, Q., Lv, K., Zhang, Z., Li, M., & Li, B. (2015). Effect of contact interface between TiO₂ and g-C₃N₄ on the photoreactivity of g-C₃N₄/TiO₂ photocatalyst: (0 0 1) vs (1 0 1) facets of TiO₂. *Applied Catalysis B: Environmental*, 164, 420–427. <https://doi.org/10.1016/j.apcatb.2014.09.043>
- Hu, F., Sun, S., Xu, H., Li, M., Hao, X., Shao, G., Wang, H., Chen, D., Lu, H., & Zhang, R. (2021). Investigation on g-C₃N₄/rGO/TiO₂ nanocomposite with enhanced photocatalytic degradation performance. *Journal of Physics and Chemistry of Solids*, 156, 110181. <https://doi.org/10.1016/j.jpcs.2021.110181>
- Hu, L., Yan, J., Wang, C., Chai, B., & Li, J. (2019). Direct electrospinning method for the construction of Z-scheme TiO₂/g-C₃N₄/RGO ternary heterojunction photocatalysts with remarkably ameliorated photocatalytic performance. *Chinese Journal of Catalysis*, 40, 458–469. [https://doi.org/10.1016/s1872-2067\(18\)63181-x](https://doi.org/10.1016/s1872-2067(18)63181-x)
- Humayun, M., Raziq, F., Khan, A., & Luo, W. (2018). Modification strategies of TiO₂ for potential applications in photocatalysis: a critical review. *Green Chemistry Letters and Reviews*, 11, 86–102. <https://doi.org/10.1080/17518253.2018.1440324>
- Iervolino, G., Zammit, I., Vaiano, V., & Rizzo, L. (2019). Limitations and prospects for wastewater treatment by UV and visible-light-active heterogeneous photocatalysis: A critical review. *Topics in Current Chemistry*, 378, 7. <https://doi.org/10.1007/s41061-019-0272-1>
- Ismael, A. M., El-Shazly, A. N., Gaber, S. E., Rashad, M. M., Kamel, A. H., & Hassan, S. S. M. (2020). Novel TiO₂/GO/CuFe₂O₄ nanocomposite: A magnetic, reusable and visible-light-driven photocatalyst for efficient photocatalytic removal of chlorinated pesticides from wastewater. *RSC Advances*, 10, 34806–34814. <https://doi.org/10.1039/d0ra02874f> 2020.
- Jiang, G., Cao, J., Chen, M., Zhang, X., & Dong, F. (2018). Photocatalytic NO oxidation on N-doped TiO₂/g-C₃N₄ heterojunction: Enhanced efficiency, mechanism and reaction pathway. *Applications of Surface Science*, 458, 77–85. <https://doi.org/10.1016/j.apsusc.2018.07.087>
- Jiang, L., Yuan, X., Pan, Y., Liang, J., Zeng, G., Wu, Z., & Wang, H. (2017). Doping of graphitic carbon nitride for photocatalysis: A review. *Applied Catalysis B: Environmental*, 217, 388–406. <https://doi.org/10.1016/j.apcatb.2017.06.003>
- Jianmin, C. T. K. N., Informatio, H. L., & Yu, A. (2016). Preparation of blue TiO₂ for visible-light-driven photocatalysis. In D. Yang (Ed.), *Titanium dioxide* (pp. 1–15). Intech. <https://doi.org/http://dx.doi.org/10.5772/intechopen.73059>
- Ji, H., Du, P., Zhao, D., Li, S., Sun, F., Duin, E. C., & Liu, W. (2020). 2D/1D graphitic carbon nitride/titanate nanotubes heterostructure for efficient photocatalysis of sulfamethazine under solar light: Catalytic “hot spots” at the rutile–anatase–titanate interfaces. *Applied Catalysis B: Environmental*, 263, 118357. <https://doi.org/10.1016/j.apcatb.2019.118357>
- Jourshabani, M., Lee, B. K., & Shariatinia, Z. (2020). From traditional strategies to Z-scheme configuration in graphitic carbon nitride photocatalysts: Recent progress and future challenges. *Applied Catalysis B: Environmental*, 276, 119157. <https://doi.org/10.1016/j.apcatb.2020.119157>
- Jo, W. K., & Natarajan, T. S. (2015). Influence of TiO₂ morphology on the photocatalytic efficiency of direct Z-scheme g-C₃N₄/TiO₂ photocatalysts for isoniazid degradation. *Chemical Engineering Journal*, 281, 549–565. <https://doi.org/10.1016/j.cej.2015.06.120>
- Kumar, A., Khan, M., He, J., & Lo, I. M. C. (2020). Recent developments and challenges in practical application of visible-light-driven TiO₂-based heterojunctions for PPCP degradation: A critical review. *Water Research*, 170, 115356. <https://doi.org/10.1016/j.watres.2019.115356>
- Kumar, A., Khan, M., Zeng, X., & Lo, I. M. C. (2018). Development of g-C₃N₄/TiO₂/Fe₃O₄@SiO₂ heterojunction via sol-gel route: A magnetically recyclable direct contact Z-scheme nanophotocatalyst for enhanced photocatalytic removal of ibuprofen from real sewage effluent under visible light. *Chemical Engineering Journal*, 353, 645–656. <https://doi.org/10.1016/j.cej.2018.07.153>
- Kumar, A., Raizada, P., Singh, P., Saini, R. V., Saini, A. K., & Hosseini-Bandegharaei, A. (2020). Perspective and status of polymeric graphitic carbon nitride based Z-scheme photocatalytic systems for sustainable photocatalytic water purification. *Chemical Engineering Journal*, 391, 123496. <https://doi.org/10.1016/j.cej.2019.123496>
- Kumar, K., & Chowdhury, A. (2020). *Use of novel nanostructured photocatalysts for the environmental sustainability of wastewater treatments*. Elsevier Ltd.
- Kumar, S., Karthikeyan, S., & Lee, A. F. (2018). g-C₃N₄-based nanomaterials for visible light-driven photocatalysis. *Catalysts*, 8, 74. <https://doi.org/10.3390/catal8020074>
- Li, C., Sun, Z., Xue, Y., Yao, G., & Zheng, S. (2016). A facile synthesis of g-C₃N₄/TiO₂ hybrid photocatalysts by sol-gel method and its enhanced photodegradation towards methylene blue under visible light. *Advanced Powder Technology*, 27, 330–337. <https://doi.org/10.1016/j.appt.2016.01.003>
- Li, C., Sun, Z., Zhang, W., Yu, C., & Zheng, S. (2018). Highly efficient g-C₃N₄/TiO₂/kaolinite composite with novel three-dimensional structure and enhanced visible light responding ability towards ciprofloxacin and S. aureus. *Applied Catalysis B: Environmental*, 220, 272–282. <https://doi.org/10.1016/j.apcatb.2017.08.044>
- Li, D.-F., Huang, W.-Q., Zou, L.-R., Pan, A., & Huang, G.-F. (2018). Mesoporous g-C₃N₄ nanosheets: Synthesis, superior adsorption capacity and photocatalytic activity. *Journal of Nanoscience and Nanotechnology*, 18, 5502–5510. <https://doi.org/10.1166/jnn.2018.15441>
- Li, J., Zhang, M., Li, X., Li, Q., & Yang, J. (2017). Effect of the calcination temperature on the visible light photocatalytic activity of direct contact Z-scheme g-C₃N₄-TiO₂ heterojunction. *Applied Catalysis B: Environmental*, 212, 106–114. <https://doi.org/10.1016/j.apcatb.2017.04.061>
- Li, R., Li, T., & Zhou, Q. (2020). Impact of titanium dioxide (TiO₂) modification on its application to pollution treatment—A review. *Catalysts*, 10, 804. <https://doi.org/10.3390/catal10070804>
- Liu, M., Wei, S., Chen, W., Gao, L., Li, X., Mao, L., & Dang, H. (2020). Construction of direct Z-scheme g-C₃N₄/TiO₂ nanorod composites for promoting photocatalytic activity. *Journal of the Chinese Chemical Society*, 67, 246–252. <https://doi.org/10.1002/jccs.201900135>
- Liu, R., Bie, Y., Qiao, Y., Liu, T., & Song, Y. (2019). Design of g-C₃N₄/TiO₂ nanotubes heterojunction for enhanced organic pollutants degradation in waste water. *Materials Letters*, 251, 126–130. <https://doi.org/10.1016/j.matlet.2019.05.065>
- Liu, X., Li, W., Hu, R., Wei, Y., Yun, W., Nian, P., Feng, J., & Zhang, A. (2020). Synergistic degradation of acid orange 7 dye by using non-thermal plasma and g-C₃N₄/TiO₂: Performance, degradation pathways and catalytic mechanism. *Chemosphere*, 249, 126093. <https://doi.org/10.1016/j.chemosphere.2020.126093>
- Liu, X., Ma, R., Zhuang, L., Hu, B., Chen, J., Liu, X., & Wang, X. (2021). Recent developments of doped g-C₃N₄ photocatalysts for the degradation of organic

- pollutants. *Critical Reviews in Environmental Science and Technology*, 51, 751–790. <https://doi.org/10.1080/10643389.2020.1734433>
- Liu, Y., Zeng, X., Hu, X., Hu, J., Wang, Z., Yin, Y., Sun, C., & Zhang, X. (2019). Two-dimensional g-C₃N₄/TiO₂ nanocomposites as vertical Z-scheme heterojunction for improved photocatalytic water disinfection. *Catalysis Today*, 335, 243–251. <https://doi.org/10.1016/j.cattod.2018.11.053>
- Li, Y., Lv, K., Ho, W., Dong, F., Wu, X., & Xia, Y. (2017). Hybridization of rutile TiO₂ (rTiO₂) with g-C₃N₄ quantum dots (CN QDs): An efficient visible-light-driven Z-scheme hybridized photocatalyst. *Applied Catalysis B: Environmental*, 202, 611–619. <https://doi.org/10.1016/j.apcatb.2016.09.055>
- Low, J., Jiang, C., Cheng, B., Wageh, S., Al-Ghamdi, A. A., & Yu, J. (2017). A review of direct Z-scheme photocatalysts. *Small Methods*, 1, 1700080. <https://doi.org/10.1002/smt.201700080>
- Low, J., Yu, J., Jaroniec, M., Wageh, S., & Al-Ghamdi, A. A. (2017). Heterojunction photocatalysts. *Advanced Materials*, 29(20), 1. <https://doi.org/10.1002/adma.201601694>
- Lu, L., Wang, G., Zou, M., Wang, J., & Li, J. (2018). Effects of calcining temperature on formation of hierarchical TiO₂/g-C₃N₄ hybrids as an effective Z-scheme heterojunction photocatalyst. *Applied Surface Science*, 441, 1012–1023. <https://doi.org/10.1016/j.apsusc.2018.02.080>
- Lu, Y., Yu, H., Chen, S., Quan, X., & Zhao, H. (2012). Integrating plasmonic nanoparticles with TiO₂ photonic crystal for enhancement of visible-light-driven photocatalysis. *Environmental Science & Technology*, 46, 1724–1730. <https://doi.org/10.1021/es202669y>
- Lu, Z., Zeng, L., Song, W., Qin, Z., Zeng, D., & Xie, C. (2017). In situ synthesis of C-TiO₂/g-C₃N₄ heterojunction nanocomposite as highly visible light active photocatalyst originated from effective interfacial charge transfer. *Applied Catalysis B: Environmental*, 202, 489–499. <https://doi.org/10.1016/j.apcatb.2016.09.052>
- Mahlambi, M. M., Ngila, C. J., & Mamba, B. B. (2015). Recent developments in environmental photocatalytic degradation of organic pollutants: The case of titanium dioxide nanoparticles—A review. *Journal of Nanomaterials*, 2015, 1–29. <https://doi.org/10.1155/2015/790173>
- Malato, S., Fernández-Ibáñez, P., Maldonado, M. I., Blanco, J., & Gernjak, W. (2009). Decontamination and disinfection of water by solar photocatalysis: Recent overview and trends. *Catalysis Today*, 147, 1–59. <https://doi.org/10.1016/j.cattod.2009.06.018>
- Manikandan, S., Karmegam, N., Subbaiya, R., Karthiga Devi, G., Arulvel, R., Ravindran, B., & Kumar Awasthi, M. (2021). Emerging nano-structured innovative materials as adsorbents in wastewater treatment. *Bioresour Technology*, 320, 124394. <https://doi.org/10.1016/j.biortech.2020.124394>
- Meng, X., & Zhang, Z. (2018). Two dimensional graphitic materials for photoelectrocatalysis: A short review. *Catalysis Today*, 315, 2–8. <https://doi.org/10.1016/j.cattod.2018.03.015>
- Miklos, D. B., Remy, C., Jekel, M., Linden, K. G., Drewes, J. E., & Hübner, U. (2018). Evaluation of advanced oxidation processes for water and wastewater treatment - A critical review. *Water Research*, 139, 118–131. <https://doi.org/10.1016/j.watres.2018.03.042>
- Mishra, A., Mehta, A., Basu, S., Shetti, N. P., Reddy, K. R., & Aminabhavi, T. M. (2019). Graphitic carbon nitride (g-C₃N₄)-based metal-free photocatalysts for water splitting: A review. *Carbon*, 149, 693–721. <https://doi.org/10.1016/j.carbon.2019.04.104>
- Mohini, R., & Lakshminarasimhan, N. (2016). Coupled semiconductor nanocomposite g-C₃N₄/TiO₂ with enhanced visible light photocatalytic activity. *Materials Research Bulletin*, 76, 370–375. <https://doi.org/10.1016/j.materresbull.2015.12.034>
- Monga, D., & Basu, S. (2019). Enhanced photocatalytic degradation of industrial dye by g-C₃N₄/TiO₂ nanocomposite: Role of shape of TiO₂. *Advanced Powder Technology*, 30, 1089–1098. <https://doi.org/10.1016/j.appt.2019.03.004>
- Moslah, C., Kandyla, M., Mousdis, G. A., Petropoulou, G., & Ksibi, M. (2018). Photocatalytic properties of titanium dioxide thin films doped with noble metals (Ag, Au, Pd, and Pt). *Phys. Status Solidi Appl. Mater. Sci.*, 215, 1–7. <https://doi.org/10.1002/pssa.201800023>
- Mousavi, M., Habibi-Yangjeh, A., & Poursan, S. R. (2018). Review on magnetically separable graphitic carbon nitride-based nanocomposites as promising visible-light-driven photocatalysts. *Journal of Materials Science Materials in Electronics*, 29, 1719–1747. <https://doi.org/10.1007/s10854-017-8166-x>
- Muhd Jukapli, N., Bagheri, S., & Bee Abd Hamid, S. (2014). Recent advances in heterogeneous photocatalytic decolorization of synthetic dyes. *Science World Journal*, 2014, 1–25. <https://doi.org/10.1155/2014/692307>
- Nadimi, M., Ziarati Saravani, A., Aroon, M. A., & Ebrahimi Pirbazari, A. (2019). Photodegradation of methylene blue by a ternary magnetic TiO₂/Fe₃O₄/graphene oxide nanocomposite under visible light. *Materials Chemistry and Physics*, 225, 464–474. <https://doi.org/10.1016/j.matchemphys.2018.11.029>
- Nasirian, M., Lin, Y. P., Bustillo-Lecompte, C. F., & Mehrvar, M. (2018). Enhancement of photocatalytic activity of titanium dioxide using non-metal doping methods under visible light: A review. *International Journal of Environmental Science and Technology*, 15, 2009–2032. <https://doi.org/10.1007/s13762-017-1618-2>
- Natarajan, T. S., Thampi, K. R., & Tayade, R. J. (2018). Visible light driven redox-mediator-free dual semiconductor photocatalytic systems for pollutant degradation and the ambiguity in applying Z-scheme concept. *Applied Catalysis B: Environmental*, 227, 296–311. <https://doi.org/10.1016/j.apcatb.2018.01.015>
- Nie, Y. C., Yu, F., Wang, L. C., Xing, Q. J., Liu, X., Pei, Y., Zou, J. P., Dai, W. L., Li, Y., & Suib, S. L. (2018). Photocatalytic degradation of organic pollutants coupled with simultaneous photocatalytic H₂ evolution over graphene quantum dots/Mn-N-TiO₂/g-C₃N₄ composite catalysts: Performance and mechanism. *Applied Catalysis B: Environmental*, 227, 312–321. <https://doi.org/10.1016/j.apcatb.2018.01.033>
- Ni, J., Wang, W., Liu, D., Zhu, Q., Jia, J., Tian, J., Li, Z., Wang, X., & Xing, Z. (2021). Oxygen vacancy-mediated sandwich-structural TiO₂-x /ultrathin g-C₃N₄/TiO₂-x direct Z-scheme heterojunction visible-light-driven photocatalyst for efficient removal of high toxic tetracycline antibiotics. *Journal of Hazardous Materials*, 408, 124432. <https://doi.org/10.1016/j.jhazmat.2020.124432>
- Nolan, N. T., Seery, M. K., Hinder, S. J., Healy, L. F., & Pillai, S. C. (2010). A systematic study of the effect of silver on the chelation of formic acid to a titanium precursor and the resulting effect on the anatase to rutile transformation of TiO₂. *Journal of Physical Chemistry C*, 114, 13026–13034. <https://doi.org/10.1021/jp1016054>
- Ong, W. J., Tan, L. L., Ng, Y. H., Yong, S. T., & Chai, S. P. (2016). Graphitic carbon nitride (g-C₃N₄)-based photocatalysts for artificial photosynthesis and environmental remediation: Are we a step closer to achieving sustainability? *Chemical Reviews*, 116, 7159–7329. <https://doi.org/10.1021/acs.chemrev.6b00075>
- Patnaik, S., Sahoo, D. P., & Parida, K. (2021). Recent advances in anion doped g-C₃N₄ photocatalysts: A review. *Carbon*, 172, 682–711. <https://doi.org/10.1016/j.carbon.2020.10.073>
- Peiris, S., Silva, H. B., Ranasinghe, K. N., Bandara, S. V., & Perera, I. R. (2021). Recent development and future prospects of TiO₂ photocatalysis. *Journal of the Chinese Chemical Society*, 68, 738–769. <https://doi.org/10.1002/jccs.202000465>
- Pelaez, M., Nolan, N. T., Pillai, S. C., Seery, M. K., Falaras, P., Kontos, A. G., Dunlop, P. S. M., Hamilton, J. W. J., Byrne, J. A., O'Shea, K., Entezari, M. H., & Dionysiou, D. D. (2012). A review on the visible light active titanium dioxide photocatalysts for environmental applications. *Applied Catalysis B: Environmental*, 125, 331–349. <https://doi.org/10.1016/j.apcatb.2012.05.036>
- Porcu, S., Castellino, M., Roppolo, I., Carbonaro, C. M., Palmas, S., Mais, L., Casula, M. F., Neretina, S., Hughes, R. A., Secci, F., & Ricci, P. C. (2020). Highly efficient visible light phenyl modified carbon nitride/TiO₂ photocatalyst for environmental applications. *Applications of Surface Science*, 531, 147394. <https://doi.org/10.1016/j.apsusc.2020.147394>
- Prakash, J., Sun, S., Swart, H. C., & Gupta, R. K. (2018). Noble metals-TiO₂ nanocomposites: From fundamental mechanisms to photocatalysis, surface enhanced Raman scattering and antibacterial applications. *Applied Materials Today*, 11, 82–135. <https://doi.org/10.1016/j.apmt.2018.02.002>
- Prasad, C., Tang, H., & Bahadur, I. (2019). Graphitic carbon nitride based ternary nanocomposites: From synthesis to their applications in photocatalysis: A recent review. *Journal of Molecular Liquids*, 281, 634–654. <https://doi.org/10.1016/j.molliq.2019.02.068>
- Putri, L. K., Tan, L. L., Ong, W. J., Chang, W. S., & Chai, S. P. (2016). Graphene oxide: Exploiting its unique properties toward visible-light-driven photocatalysis. *Applied Materials Today*, 4, 9–16. <https://doi.org/10.1016/j.apmt.2016.04.001>
- Qi, K., Cheng, B., Yu, J., & Ho, W. (2017). A review on TiO₂-based Z-scheme photocatalysts. *Chinese Journal of Catalysis*, 38, 1936–1955. [https://doi.org/10.1016/s1872-067\(17\)62962-0](https://doi.org/10.1016/s1872-067(17)62962-0)
- Rahimi, N., Pax, R. A., & Gray, E. M. (2016). Review of functional titanium oxides. I: TiO₂ and its modifications. *Progress in Solid State Chemistry*, 44, 86–105. <https://doi.org/10.1016/j.progsolidchem.2016.07.002>
- Raja, V., & Jaffar Ali, B. M. (2021). Synergy of photon up-conversion and Z-scheme mechanism in graphitic carbon nitride nanoparticles decorated g-C₃N₄-TiO₂. *Colloids and Surfaces A: Physicochemical and Engineering Aspects*, 611, 125862. <https://doi.org/10.1016/j.colsurfa.2020.125862>
- Reddy, K. R., Reddy, C. V., Nadagouda, M. N., Shetti, N. P., Jaesool, S., & Aminabhavi, T. M. (2019). Polymeric graphitic carbon nitride (g-C₃N₄)-based semiconducting nanostructured materials: Synthesis methods, properties and photocatalytic applications. *Journal of Environmental Management*, 238, 25–40. <https://doi.org/10.1016/j.jenvman.2019.02.075>
- Rehman, S., Ullah, R., Butt, A. M., & Gohar, N. D. (2009). Strategies of making TiO₂ and ZnO visible light active. *Journal of Hazardous Materials*, 170, 560–569. <https://doi.org/10.1016/j.jhazmat.2009.05.064>
- Ribeiro, A. R., Nunes, O. C., Pereira, M. F., & Silva, A. M. (2015). An overview on the advanced oxidation processes applied for the treatment of water pollutants defined in the recently launched Directive 2013/39/EU. *Environment International*, 75, 33–51. <https://doi.org/10.1016/j.envint.2014.10.027>
- Sabir, R., Waheed, A., Moazzam Ali, M., & Mushtaq, U. (2021). Graphene-based photocatalysts for organic pollutant removal from waste-water: recent progress and future challenges. *Environmental Technology Reviews*, 10, 323–341. <https://doi.org/10.1080/21622515.2021.1994658>

- Salomatina, E. V., Fukina, D. G., Koryagin, A. V., Titaev, D. N., Suleimanov, E. V., & Smirnova, L. A. (2021). Preparation and photocatalytic properties of titanium dioxide modified with gold or silver nanoparticles. *Journal of Environmental Chemical Engineering*, 9, 106078. <https://doi.org/10.1016/j.jece.2021.106078>.
- Saravanan, R., Gracia, F., & Stephen, A. (2017). Basic principles, mechanism, and challenges of photocatalysis. In: M. Khan, D. Pradhan, & Y. Sohn (Eds.), *Nanocomposites for visible light-induced photocatalysis*. Springer series on polymer and composite materials (pp. 19–40). Springer. <https://doi.org/10.1007/978-3-319-62446-4>.
- Shen, Y., Dos Santos-Garcia, A. J., & Martín de Vidales, M. J. (2020). Graphitic carbon nitride-based composite in advanced oxidation processes for aqueous organic pollutants removal: A review. *Processes*, 9(1), 66. <https://doi.org/10.3390/pr9010066>.
- Shi, L., Wang, F., & Sun, J. (2019). The preparation of spherical mesoporous g-C₃N₄ with highly improved photocatalytic performance for H₂ production and rhodamine B degradation. *Materials Research Bulletin*, 113, 115–121. <https://doi.org/10.1016/j.matresbull.2019.01.028>.
- Singh, R., & Dutta, S. (2018). Synthesis and characterization of solar photoactive TiO₂ nanoparticles with enhanced structural and optical properties. *Advanced Powder Technology*, 29, 211–219. <https://doi.org/10.1016/j.appt.2017.11.005>.
- Sridharan, K., Jang, E., & Park, T. J. (2013). Novel visible light active graphitic C₃N₄-TiO₂ composite photocatalyst: Synergistic synthesis, growth and photocatalytic treatment of hazardous pollutants. *Applied Catalysis B: Environmental*, 142–143, 718–728. <https://doi.org/10.1016/j.apcatb.2013.05.077>.
- Starukh, H., & Praus, P. (2020). Doping of graphitic carbon nitride with non-metal elements and its applications in photocatalysis. *Catalysts*, 10, 1119. <https://doi.org/10.3390/catal10101119>.
- Sudhaik, A., Raizada, P., Shandilya, P., Jeong, D. Y., Lim, J. H., & Singh, P. (2018). Review on fabrication of graphitic carbon nitride based efficient nanocomposites for photodegradation of aqueous phase organic pollutants. *Journal of Industrial and Engineering Chemistry*, 67, 28–51. <https://doi.org/10.1016/j.jiec.2018.07.007>.
- Sui, G., Li, J., Du, L., Zhuang, Y., Zhang, Y., Zou, Y., & Li, B. (2020). Preparation and characterization of g-C₃N₄/Ag-TiO₂ ternary hollowsphere nanoheterojunction catalyst with high visible light photocatalytic performance. *Journal of Alloys and Compounds*, 823, 153851. <https://doi.org/10.1016/j.jallcom.2020.153851>.
- Sun, Z., Wang, H., Wu, Z., & Wang, L. (2018). g-C₃N₄ based composite photocatalysts for photocatalytic CO₂ reduction. *Catalysis Today*, 300, 160–172. <https://doi.org/10.1016/j.cattod.2017.05.033>.
- Sutar, R. S., Barkul, R. P., Delekar, S. D., & Patil, M. K. (2020). Sunlight assisted photocatalytic degradation of organic pollutants using g-C₃N₄-TiO₂ nanocomposites. *Arabian Journal of Chemistry*, 13, 4966–4977. <https://doi.org/10.1016/j.arabj.2020.01.019>.
- Su, Y., Chen, P., Wang, F., Zhang, Q., Chen, T., Wang, Y., Yao, K., Lv, W., & Liu, G. (2017). Decoration of TiO₂/g-C₃N₄ Z-scheme by carbon dots as a novel photocatalyst with improved visible-light photocatalytic performance for the degradation of enrofloxacin. *RSC Advances*, 7, 34096–34103. <https://doi.org/10.1039/c7ra05485h>.
- Tada, H., Mitsui, T., Kiyonaga, T., Akita, T., & Tanaka, K. (2006). All-solid-state Z-scheme in CdS-Au-TiO₂ three-component nanojunction system. *Nature Materials*, 5, 782–786. <https://doi.org/10.1038/nmat1734>.
- Tahir, M., Tasleem, S., & Tahir, B. (2020). Recent development in band engineering of binary semiconductor materials for solar driven photocatalytic hydrogen production. *International Journal of Hydrogen Energy*, 45, 15985–16038. <https://doi.org/10.1016/j.ijhydene.2020.04.071>.
- Tan, J., Li, Z., Li, J., Wu, J., Yao, X., & Zhang, T. (2021). Graphitic carbon nitride-based materials in activating persulfate for aqueous organic pollutants degradation: A review on materials design and mechanisms. *Chemosphere*, 262, 127675. <https://doi.org/10.1016/j.chemosphere.2020.127675>.
- Thines, R. K., Mubarak, N. M., Nizamuddin, S., Sahu, J. N., Abdullah, E. C., & Ganesan, P. (2017). Application potential of carbon nanomaterials in water and wastewater treatment: A review. *Journal of the Taiwan Institute of Chemical Engineers*, 72, 116–133. <https://doi.org/10.1016/j.jtice.2017.01.018>.
- Thomas, A., Fischer, A., Goettmann, F., Antonietti, M., Müller, J. O., Schlögl, R., & Carlsson, J. M. (2008). Graphitic carbon nitride materials: Variation of structure and morphology and their use as metal-free catalysts. *Journal of Materials Chemistry*, 18, 4893–4908. <https://doi.org/10.1039/b800274f>.
- Tobaldi, D. M., Pullar, R. C., Gualtieri, A. F., Seabra, M. P., & Labrincha, J. A. (2013). Sol-gel synthesis, characterisation and photocatalytic activity of pure, W-, Ag- and W/Ag co-doped TiO₂ nanopowders. *Chemical Engineering Journal*, 214, 364–375. <https://doi.org/10.1016/j.cej.2012.11.018>.
- Tsang, C. H. A., Li, K., Zeng, Y., Zhao, W., Zhang, T., Zhan, Y., Xie, R., Leung, D. Y. C., & Huang, H. (2019). Titanium oxide based photocatalytic materials development and their role of in the air pollutants degradation: Overview and forecast. *Environment International*, 125, 200–228. <https://doi.org/10.1016/j.envint.2019.01.015>.
- Varma, K. S., Tayade, R. J., Shah, K. J., Joshi, P. A., Shukla, A. D., & Gandhi, V. G. (2020). Photocatalytic degradation of pharmaceutical and pesticide compounds (PPCs) using doped TiO₂ nanomaterials: A review. *Water-Energy Nexus*, 3, 46–61. <https://doi.org/10.1016/j.wen.2020.03.008>.
- Voon, S., Ong, W., Tan, L., Yong, S., & Chai, S. (2016). Graphene-based semiconductor materials for photocatalytic applications. In M. Aliofkhazraei, N. Ali, W. I. Milne, C. S. Ozkan, S. Mitura, & J. L. Gervasoni (Eds.), *Graphene Science Handbook: Size-Dependent Properties* (pp. 331–348). CRC Press.
- Wang, K., Li, Q., Liu, B., Cheng, B., Ho, W., & Yu, J. (2015). Sulfur-doped g-C₃N₄ with enhanced photocatalytic CO₂-reduction performance. *Applied Catalysis B: Environmental*, 176–177, 44–52. <https://doi.org/10.1016/j.apcatb.2015.03.045>.
- Wang, P., Huang, B., Dai, Y., & Whangbo, M. H. (2012). Plasmonic photocatalysts: Harvesting visible light with noble metal nanoparticles. *Physical Chemistry Chemical Physics*, 14, 9813–9825. <https://doi.org/10.1039/c2cp40823f>.
- Wang, X. J., Yang, W. Y., Li, F. T., Xue, Y. B., Liu, R. H., & Hao, Y. J. (2013). in situ microwave-assisted synthesis of porous N-TiO₂/g-C₃N₄ heterojunctions with enhanced visible-light photocatalytic properties. *Industrial & Engineering Chemistry Research*, 52, 17140–17150. <https://doi.org/10.1021/ie402820v>.
- Wang, X., Liu, G., Chen, Z. G., Li, F., Wang, L., Lu, G. Q., & Cheng, H. M. (2009). Enhanced photocatalytic hydrogen evolution by prolonging the lifetime of carriers in ZnO/CdS heterostructures. *Chemical Communications*, 23, 3452–3454. <https://doi.org/10.1039/b904668b>.
- Wang, X., & Liu, M. (2019). Photocatalytic enhancement mechanism of direct Z-scheme heterojunction O-g-C₃N₄/Fe-TiO₂ under visible-light irradiation. *Applications of Surface Science*, 485, 353–360. <https://doi.org/10.1016/j.apsusc.2019.04.207>.
- Wang, X., Maeda, K., Chen, X., Takanabe, K., Domen, K., Hou, Y., Fu, X., & Antonietti, M. (2009). Polymer semiconductors for artificial photosynthesis: hydrogen evolution by mesoporous graphitic carbon nitride with visible light. *Journal of the American Chemical Society*, 131, 1680–1681.
- Wang, Y., Wang, X., & Antonietti, M. (2012). Polymeric graphitic carbon nitride as a heterogeneous organocatalyst: From photochemistry to multipurpose catalysis to sustainable chemistry. *Angewandte Chemie International Edition*, 51, 68–89. <https://doi.org/10.1002/anie.201101182>.
- Wen, J., Li, X., Liu, W., Fang, Y., Xie, J., & Xu, Y. (2015). Photocatalysis fundamentals and surface modification of TiO₂ nanomaterials. *Chinese Journal of Catalysis*, 36, 2049–2070. [https://doi.org/10.1016/s1872-2067\(15\)60999-8](https://doi.org/10.1016/s1872-2067(15)60999-8).
- Wen, J., Xie, J., Chen, X., & Li, X. (2017). A review on g-C₃N₄-based photocatalysts. *Applications of Surface Science*, 391, 72–123. <https://doi.org/10.1016/j.apsusc.2016.07.030>.
- Wu, F., Li, X., Liu, W., & Zhang, S. (2017). Highly enhanced photocatalytic degradation of methylene blue over the indirect all-solid-state Z-scheme g-C₃N₄-RGO-TiO₂ nanoheterojunctions. *Applications of Surface Science*, 405, 60–70. <https://doi.org/10.1016/j.apsusc.2017.01.285>.
- Xiao, L., Liu, T., Zhang, M., Li, Q., & Yang, J. (2019). Interfacial construction of zero-dimensional/one-dimensional g-C₃N₄ nanoparticles/TiO₂ nanotube arrays with Z-scheme heterostructure for improved photoelectrochemical water splitting. *ACS Sustainable Chemistry & Engineering*, 7, 2483–2491. <https://doi.org/10.1021/acssuschemeng.8b05392>.
- Xiao, X., Wang, Y., Bo, Q., Xu, X., & Zhang, D. (2020). One-step preparation of sulfur-doped porous g-C₃N₄ for enhanced visible light photocatalytic performance. *Journal of the Chemical Society, Dalton Transactions*, 49(24), 8041–8050. <https://doi.org/10.1039/d0dt00299b>.
- Xie, L., Du, T., Wang, J., Ma, Y., Ni, Y., Liu, Z., Zhang, L., Yang, C., & Wang, J. (2021). Recent advances on heterojunction-based photocatalysts for the degradation of persistent organic pollutants. *Chemical Engineering Journal*, 426, 130617. <https://doi.org/10.1016/j.cej.2021.130617>.
- Xu, B., Ahmed, M. B., Zhou, J. L., Altaee, A., Xu, G., & Wu, M. (2018). Graphitic carbon nitride based nanocomposites for the photocatalysis of organic contaminants under visible irradiation: Progress, limitations and future directions. *The Science of the Total Environment*, 633, 546–559. <https://doi.org/10.1016/j.scitotenv.2018.03.206>.
- Xu, J., Dong, Z., Hu, T., Peng, Y., Situ, Y., & Huang, H. (2019). Construction of TiO₂-Fe-C₃N₄ compound: Promotion of interfacial charge transfer effect through facile energy level alignment. *Journal of Alloys and Compounds*, 781, 140–148. <https://doi.org/10.1016/j.jallcom.2018.11.409>.
- Xu, Q., Zhang, L., Yu, J., Wageh, S., Al-Ghamdi, A. A., & Jaronec, M. (2018). Direct Z-scheme photocatalysts: Principles, synthesis, and applications. *Materials Today*, 21, 1042–1063. <https://doi.org/10.1016/j.mattod.2018.04.008>.
- Yadav, S., & Jaiswar, G. (2017). Review on undoped/doped TiO₂ nanomaterial; syntheses and photocatalytic and antimicrobial activity. *Journal of the Chinese Chemical Society*, 64, 103–116. <https://doi.org/10.1002/jccs.201600735>.
- Yahya, N., Aziz, F., Jamaludin, N. A., A. Mutalib, M., Ismail, A. F., W. Salleh, W. N., Jaafar, J., Yusof, N. A., & Ludin, N. (2018). A review of integrated photocatalyst adsorbents for wastewater treatment. *Journal of Environmental Chemical Engineering*, 6, 7411–7425. <https://doi.org/10.1016/j.jece.2018.06.051>.
- Yang, L., Bai, X., Shi, J., Du, X., Xu, L., & Jin, P. (2019). Quasi-full-visible-light absorption by D35-TiO₂/g-C₃N₄ for synergistic persulfate activation towards efficient photodegradation of micropollutants. *Applied Catalysis B: Environmental*, 256, 117759. <https://doi.org/10.1016/j.apcatb.2019.117759>.
- Yao, Y., Cai, Y., Lu, F., Wei, F., Wang, X., & Wang, S. (2014). Magnetic recoverable MnFe₂O₄ and MnFe₂O₄-graphene hybrid as heterogeneous catalysts of

- peroxymonosulfate activation for efficient degradation of aqueous organic pollutants. *Journal of Hazardous Materials*, 270, 61–70. <https://doi.org/10.1016/j.jhazmat.2014.01.027>
- Ye, S., Wang, R., Wu, M. Z., & Yuan, Y. P. (2015). A review on g-C₃N₄ for photocatalytic water splitting and CO₂ reduction. *Applications of Surface Science*, 358, 15–27. <https://doi.org/10.1016/j.apsusc.2015.08.173>
- Younis, S., & Kim, K. H. (2020). Heterogeneous photocatalysis scalability for environmental remediation: Opportunities and challenges. *Catalysts*, 10, 1109. <https://doi.org/10.3390/catal10101109>
- Yu, J., Wang, S., Low, J., & Xiao, W. (2013). Enhanced photocatalytic performance of direct Z-scheme g-C₃N₄-TiO₂ photocatalysts for the decomposition of formaldehyde in air. *Physical Chemistry Chemical Physics*, 15, 16883. <https://doi.org/10.1039/c3cp53131g>
- Zhang, J., Zhou, P., Liu, J., & Yu, J. (2014). New understanding of the difference of photocatalytic activity among anatase, rutile and brookite TiO₂. *Physical Chemistry Chemical Physics*, 16, 20382–20386. <https://doi.org/10.1039/c4cp02201g>
- Zhang, J. J., Fang, S. S., Mei, J. Y., Zheng, G. P., Zheng, X. C., & Guan, X. X. (2018). High-efficiency removal of rhodamine B dye in water using g-C₃N₄ and TiO₂ co-hybridized 3D graphene aerogel composites. *Separation and Purification Technology*, 194, 96–103. <https://doi.org/10.1016/j.seppur.2017.11.035>
- Zhang, L., Ni, C., Jiu, H., Xie, C., Yan, J., & Qi, G. (2017). One-pot synthesis of Ag-TiO₂/reduced graphene oxide nanocomposite for high performance of adsorption and photocatalysis. *Ceramics International*, 43, 5450–5456. <https://doi.org/10.1016/j.ceramint.2017.01.041>
- Zhang, S., Gu, P., Ma, R., Luo, C., Wen, T., Zhao, G., Cheng, W., & Wang, X. (2019). Recent developments in fabrication and structure regulation of visible-light-driven g-C₃N₄-based photocatalysts towards water purification: A critical review. *Catalysis Today*, 335, 65–77. <https://doi.org/10.1016/j.cattod.2018.09.013>
- Zhang, W., Mohamed, A. R., & Ong, W. (2020). Z-Scheme photocatalytic systems for carbon dioxide reduction: Where are we now? *Angewandte Chemie International Edition*, 59, 22894–22915. <https://doi.org/10.1002/anie.201914925>
- Zhang, X., Li, L., Zeng, Y., Liu, F., Yuan, J., Li, X., Yu, Y., Zhu, X., Xiong, Z., Yu, H., & Xie, Y. (2019). TiO₂/graphitic carbon nitride nanosheets for the photocatalytic degradation of Rhodamine B under simulated sunlight. *ACS Applied Nano Materials*, 2, 7255–7265. <https://doi.org/10.1021/acsanm.9b01739>
- Zhao, L., Xu, H., Jiang, B., & Huang, Y. (2017). Synergetic photocatalytic nanostructures based on Au/TiO₂/reduced graphene oxide for efficient degradation of organic pollutants. *Particle and Particle Systems Characterization*, 34, 1600323. <https://doi.org/10.1002/ppsc.201600323>
- Zhao, W., Yang, X., Liu, C., Qian, X., Wen, Y., Yang, Q., Sun, T., Chang, W., Liu, X., & Chen, Z. (2020). Facile construction of all-solid-state Z-scheme G-C₃N₄/TiO₂ thin film for the efficient visible-light degradation of organic pollutant. *Nanomaterials*, 10(4), 600. <https://doi.org/10.3390/nano10040600>
- Zhou, D., Chen, Z., Yang, Q., Dong, X., Zhang, J., & Qin, L. (2016). In-situ construction of all-solid-state Z-scheme g-C₃N₄/TiO₂ nanotube arrays photocatalyst with enhanced visible-light-induced properties. *Solar Energy Materials and Solar Cells*, 157, 399–405. <https://doi.org/10.1016/j.solmat.2016.07.007>
- Zhou, D., Chen, Z., Yang, Q., Shen, C., Tang, G., Zhao, S., Zhang, J., Chen, D., Wei, Q., & Dong, X. (2016). Facile construction of g-C₃N₄ nanosheets/TiO₂ nanotube arrays as Z-scheme photocatalyst with enhanced visible-light performance. *ChemCatChem*, 8, 3064–3073. <https://doi.org/10.1002/cctc.201600828>
- Zhou, D., Yu, B., Chen, Q., Shi, H., Zhang, Y., Li, D., Yang, X., Zhao, W., Liu, C., Wei, G., & Chen, Z. (2020). Improved visible light photocatalytic activity on Z-scheme g-C₃N₄ decorated TiO₂ nanotube arrays by a simple impregnation method. *Materials Research Bulletin*, 124, 110757. <https://doi.org/10.1016/j.materresbull.2019.110757>
- Zhou, L., Wang, L., Zhang, J., Lei, J., & Liu, Y. (2017). The preparation, and applications of g-C₃N₄/TiO₂ heterojunction catalysts—A review. *Research on Chemical Intermediates*, 43, 2081–2101. <https://doi.org/10.1007/s11164-016-2748-8>
- Zhou, L., Zhang, H., Sun, H., Liu, S., Tade, M. O., Wang, S., & Jin, W. (2016). Recent advances in non-metal modification of graphitic carbon nitride for photocatalysis: A historic review. *Catalysis Science & Technology*, 6, 7002–7023. <https://doi.org/10.1039/c6cy01195k>
- Zhou, Z., Yuan, S., & Wang, J. (2021). Theoretical progress on direct Z-scheme photocatalysis of two-dimensional heterostructures. *Frontiers in Physics*, 16, 43203. <https://doi.org/10.1007/s11467-021-1054-0>
- Zhu, J., Xiao, P., Li, H., & Carabineiro, S. A. C. (2014). Graphitic carbon nitride: Synthesis, properties, and applications in catalysis. *ACS Applied Materials & Interfaces*, 6, 16449–16465. <https://doi.org/10.1021/am502925j>